




**FLUOROPOLYMER INSULATED  
WIRES AND CABLES,  
LOW FREQUENCY, 600V, -200 TO +200 °C,  
BASED ON TYPE CSWL  
ESCC Detail Specification No. 3901/024**

**ISSUE 1  
October 2002**



	ESCC Detail Specification		PAGE ii ISSUE 1
---	---------------------------	--	--------------------

### **LEGAL DISCLAIMER AND COPYRIGHT**

European Space Agency, Copyright © 2002. All rights reserved.

The European Space Agency disclaims any liability or responsibility, to any person or entity, with respect to any loss or damage caused, or alleged to be caused, directly or indirectly by the use and application of this ESCC publication.

This publication, without the prior permission of the European Space Agency and provided that it is not used for a commercial purpose, may be:

- copied in whole in any medium without alteration or modification.
- copied in part, in any medium, provided that the ESCC document identification, comprising the ESCC symbol, document number and document issue, is removed.



europaean space agency  
agence spatiale européenne

Pages 1 to 20

**FLUOROPOLYMER INSULATED  
WIRES AND CABLES,  
LOW FREQUENCY, 600V, -200 TO +200 °C,  
BASED ON TYPE CSWL  
ESA/SCC Detail Specification No. 3901/024**



**space components  
coordination group**

Issue/Rev.	Date	Approved by	
		SCCG Chairman	ESA Director General or his Deputy
Issue 1	March 2002		



**SCC**

ESA/SCC Detail Specification  
No. 3901/024

PAGE 2  
ISSUE 1

DOCUMENTATION CHANGE NOTICE

Rev. Letter	Rev. Date	Reference	CHANGE Item	Approved DCR No.

**SCC**

ESA/SCC Detail Specification

No. 3901/024

PAGE 3

ISSUE 1

**TABLE OF CONTENTS**

	<u>Page</u>
<b>1. <u>GENERAL</u></b>	<b>5</b>
1.1 Scope	5
1.2 Component Type Variants	5
1.3 Maximum Ratings	5
1.4 Parameter Derating Information	5
1.5 Physical Characteristics	5
1.6 Functional Diagram	5
<b>2. <u>APPLICABLE DOCUMENTS</u></b>	<b>5</b>
<b>3. <u>TERMS, DEFINITIONS, ABBREVIATIONS, SYMBOLS AND UNITS</u></b>	<b>12</b>
<b>4. <u>REQUIREMENTS</u></b>	<b>12</b>
4.1 General	12
4.2 Deviations from Generic Specification	12
4.2.1 Deviations from Special In-process Controls	12
4.2.2 Deviations from Final Production Tests	12
4.2.3 Deviations from Burn-in Tests	12
4.2.4 Deviations from Qualification Tests	12
4.2.5 Deviations from Lot Acceptance Tests	12
4.3 Mechanical Requirements	13
4.3.1 Dimension Check	13
4.3.2 Weight	13
4.4 Materials and Finishes	13
4.4.1 Conductor	14
4.4.2 Insulation	14
4.4.3 Shield	14
4.4.4 Jacket	15
4.4.5 Construction of Multicore Cables	15
4.4.6 Colour-coding	15
4.5 Marking	15
4.5.1 General	15
4.5.2 The SCC Component Number	16
4.5.3 Characteristics	16
4.5.4 Traceability Information	16
4.5.5 Additional Marking	16
4.6 Electrical Measurements	16
4.6.1 Electrical Measurements at Room Temperature	16
4.6.2 Electrical Measurements at High and Low Temperatures	16
4.6.3 Circuits for Electrical Measurements	16
4.7 Burn-in Tests	16
4.8 Environmental and Endurance Tests	16
4.8.1 Mechanical Properties of Conductor	16
4.8.2 Accelerated Ageing	16
4.8.3 Wrap Test at Ambient Temperature	17
4.8.4 Voltage Test	18
4.8.5 Shrinkage	18
4.8.6 Blocking	18
4.8.7 Cold Bend Test	18
4.8.8 Cut-through Resistance	18
4.8.9 Notch Resistance	18



	<u>Page</u>
4.8.10 Resistance to Fluids	18
4.8.11 Surface Resistance	18
4.8.12 Abrasion Resistance	18
4.8.13 Soldering	19
4.8.14 Solderability	19
4.8.15 Radiation Resistance	19
4.8.16 Overload Resistance	19
4.8.17 Long-term Ageing Test	19
4.8.18 Antony and Brown Test	19

**TABLES**



1(a) Type Variants	6
1(b) Maximum Ratings	10
A Mandrel Diameters and Loads for Finished Wires	17
B Mandrel Diameters and Loads for Shielded and Jacketed Cables	17
C Mandrel Diameters and Loads for Finished Wires or Cores	18
2 Electrical Measurements at Room Temperature	19

**FIGURES**

1 Parameter Derating Information	10
2 Physical Characteristics	11

**APPENDICES (Applicable to specific Manufacturers only)**

'A' Agreed Deviations for Gore (D)	20
------------------------------------	----

		<p style="text-align: center;">ESA/SCC Detail Specification No. 3901/024</p>		<p>PAGE 5 ISSUE 1</p>
--	--	--	--	---------------------------

1. GENERAL

1.1 SCOPE

This specification details the ratings, physical and electrical characteristics, test and inspection data for Fluoropolymer Insulated Wires and Cables, Low Frequency, 600V, -200 to +200 °C, based on Type CSWL.

It shall be read in conjunction with ESA/SCC Generic Specification No. 3901, the requirements of which are supplemented herein.

1.2 COMPONENT TYPE VARIANTS

Variants of the basic types of wires and cables specified herein, which are also covered by this specification, are listed in Table 1(a).

1.3 MAXIMUM RATINGS

The maximum ratings, applicable to the finished wires and cables specified herein, which shall not be exceeded at any time during use or storage in controlled space environment, are scheduled in Table 1(b).

1.4 PARAMETER DERATING INFORMATION

The derating information applicable to the finished wires and cables specified herein is as follows:

- The maximum current for each wire used in a bundle shall be:-

$$I_{Bmax} = I_{max} \times \frac{29 - n}{28} \quad (\text{for } 1 \leq n \leq 15)$$

$$I_{Bmax} = \frac{I_{max}}{2} \quad (\text{for } n > 15)$$

where n = number of wires in the bundle.

- The temperature derating information is shown in Figure 1 with maximum current  $I_{max}$  for a single wire.
- The derating factors contained herein indicate maximum stress values and do not preclude further derating.

1.5 PHYSICAL CHARACTERISTICS

The physical characteristics of the wires and cables specified herein are shown in Figure 2 and Table 1(a).

1.6 FUNCTIONAL DIAGRAM

Not applicable.

2. APPLICABLE DOCUMENTS

The following documents form part of this specification and shall be read in conjunction with it:

- ESA/SCC Generic Specification No. 3901, Wires and Cables, Electrical, 600V, Low Frequency.
- ISO 2635, Conductors for General Purpose Aircraft Electrical Cables and Aerospace Applications - Dimensions and Characteristics. The issue which is in effect at the time of order placement shall apply.



**SCS**

ESA/SCC Detail Specification

No. 3901/024

PAGE 6

ISSUE 1

**TABLE 1(a) - TYPE VARIANTS**

VARIANT No.	SHIELDED		No. OF CORES	WIRE SIZE ISO/AWG (Note 1)	STRANDING No. OF STRANDS x DIAMETER (mm)	CONDUCTOR CHARACTERISTICS			SHIELD STRAND Ø (mm)	CORE MAX Ø (mm)	FINISHED WIRE OR CABLE CHARACTERISTICS	
	YES	NO				MAX Ø (mm)	NOM SECT. (mm <sup>2</sup> )	MAX OHMIC RESISTANCE (Ω/km)			MAX Ø (mm)	MAX WEIGHT (kg/km)
01	-	x	1	-/30	7x0.102	0.32	0.057	375	-	-	0.75	1.3
02	-	x	1	-/28	7x0.127	0.39	0.09	253	-	-	0.85	1.7
03	-	x	1	001/26	19x0.1	0.47	0.15	157	-	-	1.0	2.2
04	-	x	1	002/24	19x0.12	0.58	0.25	111	-	-	1.15	3.1
05	-	x	1	004/22	19x0.15	0.76	0.4	58	-	-	1.3	4.4
06	-	x	1	006/20	19x0.20	0.99	0.6	32	-	-	1.55	7.4
07	-	x	1	012/16	19x0.30	1.49	1.2	14	-	-	2.2	17
08	-	x	1	030/12	37x0.32	2.18	3.0	7.0	-	-	3.0	33
09	-	x	2	-/30	7x0.102	0.32	0.057	383	-	0.75	1.5	2.7
10	-	x	2	-/28	7x0.127	0.39	0.09	258	-	0.85	1.7	3.5
11	-	x	2	001/26	19x0.1	0.47	0.15	170	-	1.0	2.0	4.6
12	-	x	2	002/24	19x0.12	0.58	0.25	120	-	1.15	2.3	6.5
13	-	x	2	004/22	19x0.15	0.76	0.4	63	-	1.3	2.6	9.2
14	-	x	2	006/20	19x0.20	0.99	0.6	35	-	1.55	3.1	15.5
15	-	x	2	012/16	19x0.30	1.49	1.2	15	-	2.2	4.4	35.7
16	-	x	2	030/12	37x0.32	2.18	3.0	7.5	-	3.0	6.0	69.3

NOTES: See Page 9.





**SCC**

ESA/SCC Detail Specification

No. 3901/024

PAGE 7

ISSUE 1

**TABLE 1(a) - TYPE VARIANTS (CONTINUED)**

VARIANT No.	SHIELDED		No. OF CORES	WIRE SIZE ISO/AWG (Note 1)	STRANDING No. OF STRANDS x DIAMETER (mm)	CONDUCTOR CHARACTERISTICS			SHIELD STRAND Ø (mm)	CORE MAX Ø (mm)	FINISHED WIRE OR CABLE CHARACTERISTICS	
	YES	NO				MAX Ø (mm)	NOM SECT. (mm <sup>2</sup> )	MAX OHMIC RESISTANCE (Ω/km)			MAX Ø (mm)	MAX WEIGHT (kg/km)
17	-	x	3	- /30	7x0.102	0.32	0.057	384	-	0.75	1.6	4.1
18	-	x	3	- /28	7x0.127	0.39	0.09	259	-	0.85	1.8	5.3
19	-	x	3	001/26	19x0.1	0.47	0.15	171	-	1.0	2.2	6.9
20	-	x	3	002/24	19x0.12	0.58	0.25	121	-	1.15	2.5	9.8
21	-	x	3	004/22	19x0.15	0.76	0.4	64	-	1.3	2.8	13.9
22	-	x	3	006/20	19x0.20	0.99	0.6	37	-	1.55	3.3	23.3
23	-	x	3	012/16	19x0.30	1.49	1.2	15	-	2.2	4.7	53.6
24	-	x	3	030/12	37x0.32	2.18	3.0	7.5	-	3.0	6.5	104
25	-	x	4	- /30	7x0.102	0.32	0.057	385	-	0.75	1.8	5.4
26	-	x	4	- /28	7x0.127	0.39	0.09	260	-	0.85	2.0	7.1
27	-	x	4	001/26	19x0.1	0.47	0.15	171	-	1.0	2.4	9.2
28	-	x	4	002/24	19x0.12	0.58	0.25	122	-	1.15	2.8	13
29	-	x	4	004/22	19x0.15	0.76	0.4	64	-	1.3	3.1	18.5
30	-	x	4	006/20	19x0.20	0.99	0.6	37	-	1.55	3.7	31.1
31	-	x	4	012/16	19x0.30	1.49	1.2	16	-	2.2	5.3	71.4
32	-	x	4	030/12	37x0.32	2.18	3.0	7.9	-	3.0	7.2	138.6

NOTES: See Page 9.



**SCC**

ESA/SCC Detail Specification

No. 3901/024

PAGE 8

ISSUE 1

**TABLE 1(a) - TYPE VARIANTS (CONTINUED)**

VARIANT No.	SHIELDED		No. OF CORES	WIRE SIZE ISO/AWG (Note 1)	STRANDING No. OF STRANDS x DIAMETER (mm)	CONDUCTOR CHARACTERISTICS			SHIELD STRAND Ø (mm)	CORE MAX Ø (mm)	FINISHED WIRE OR CABLE CHARACTERISTICS	
	YES	NO				MAX Ø (mm)	NOM SECT. (mm <sup>2</sup> )	MAX OHMIC RESISTANCE (Ω/km)			MAX Ø (mm)	MAX WEIGHT (kg/km)
33	X	-	1	-/30	7x0.102	0.32	0.057	383	0.079	0.75	1.35	4.3
34	X	-	1	-/28	7x0.127	0.39	0.09	258	0.079	0.85	1.45	5.0
35	X	-	1	001/26	19x0.1	0.47	0.15	170	0.079	1.0	1.6	6.0
36	X	-	1	002/24	19x0.12	0.58	0.25	120	0.079	1.15	1.75	7.3
37	X	-	1	004/22	19x0.15	0.76	0.4	63	0.079	1.3	1.9	9.1
38	X	-	1	006/20	19x0.20	0.99	0.6	35	0.079	1.55	2.15	12.8
39	X	-	1	012/16	19x0.30	1.49	1.2	15	0.079	2.2	2.8	24
40	X	-	1	030/12	37x0.32	2.18	3.0	7.5	0.079	3.0	3.6	42.8
41	X	-	2	-/30	7x0.102	0.32	0.057	383	0.079	0.75	2.1	7.3
42	X	-	2	-/28	7x0.127	0.39	0.09	258	0.079	0.85	2.3	8.5
43	X	-	2	001/26	19x0.1	0.47	0.15	170	0.079	1.0	2.6	10
44	X	-	2	002/24	19x0.12	0.58	0.25	120	0.079	1.15	2.9	12.5
45	X	-	2	004/22	19x0.15	0.76	0.4	63	0.079	1.3	3.2	16
46	X	-	2	006/20	19x0.20	0.99	0.6	35	0.079	1.55	3.7	24.2
47	X	-	2	012/16	19x0.30	1.49	1.2	15	0.079	2.2	5.0	44.5
48	X	-	2	030/12	37x0.32	2.18	3.0	7.5	0.079	3.0	6.6	81

NOTES: See Page 9.



ESA/SCC Detail Specification

No. 3901/024

PAGE 9

ISSUE 1

TABLE 1(a) - TYPE VARIANTS (CONTINUED)

VARIANT No.	SHIELDED		No. OF CORES	WIRE SIZE ISO/AWG (Note 1)	STRANDING No. OF STRANDS x DIAMETER (mm)	CONDUCTOR CHARACTERISTICS			SHIELD STRAND Ø (mm)	CORE MAX Ø (mm)	FINISHED WIRE OR CABLE CHARACTERISTICS	
	YES	NO				MAX Ø (mm)	NOM SECT. (mm <sup>2</sup> )	MAX OHMIC RESISTANCE (Ω/km)			MAX Ø (mm)	MAX WEIGHT (kg/km)
49	x	-	3	- /30	7x0.102	0.32	0.057	386	0.079	0.75	2.2	9.0
50	x	-	3	- /28	7x0.127	0.39	0.09	259	0.079	0.85	2.4	10.6
51	x	-	3	001/26	19x0.1	0.47	0.15	171	0.079	1.0	2.8	12.7
52	x	-	3	002/24	19x0.12	0.58	0.25	121	0.079	1.15	3.1	15.9
53	x	-	3	004/22	19x0.15	0.76	0.4	64	0.079	1.3	3.4	21
54	x	-	3	006/20	19x0.20	0.99	0.6	37	0.079	1.55	3.9	33
55	x	-	3	012/16	19x0.30	1.49	1.2	15	0.079	2.2	5.3	62.2
56	x	-	3	030/12	37x0.32	2.18	3.0	7.5	0.079	3.0	7.0	115.5
57	x	-	4	- /30	7x0.102	0.32	0.057	386	0.079	0.75	2.4	10.9
58	x	-	4	- /28	7x0.127	0.39	0.09	260	0.079	0.85	2.6	13
59	x	-	4	001/26	19x0.1	0.47	0.15	171	0.079	1.0	3.0	15.7
60	x	-	4	002/24	19x0.12	0.58	0.25	122	0.079	1.15	3.4	20.2
61	x	-	4	004/22	19x0.15	0.76	0.4	64	0.079	1.3	3.7	26.4
62	x	-	4	006/20	19x0.20	0.99	0.6	37	0.079	1.55	4.3	42
63	x	-	4	012/16	19x0.30	1.49	1.2	16	0.079	2.2	5.9	80.7
64	x	-	4	030/12	37x0.32	2.18	3.0	7.9	0.079	3.0	7.8	151.5

NOTES

1. Where given, in accordance with ISO2653. AWG sizes are for reference only when ISO sizes are shown.




**TABLE 1(b) - MAXIMUM RATINGS**

NO	CHARACTERISTICS	SYMBOL	MAXIMUM RATING	UNIT	REMARKS
1	Voltage	$V_p$	600	Vrms	
2	Maximum Current (Note 1)	$I_{max}$	1.3 1.5 2.5 3.5 5.0 7.5 13 23	A	For AWG 30 28 26 24 22 20 16 12
3	Operating Temperature Range	$T_{amb}$	-200 to +200	°C	
4	Storage Temperature Range	$T_{stg}$	-200 to +200	°C	

**NOTES**

- The above specified current will generate a temperature rise of approximately 50°C above ambient temperature in a vacuum environment. Precautions shall be taken to prevent the total temperature of the wire (ambient plus rise) exceeding the continuous operating temperature of the wire.


**FIGURE 1 - PARAMETER DERATING INFORMATION**

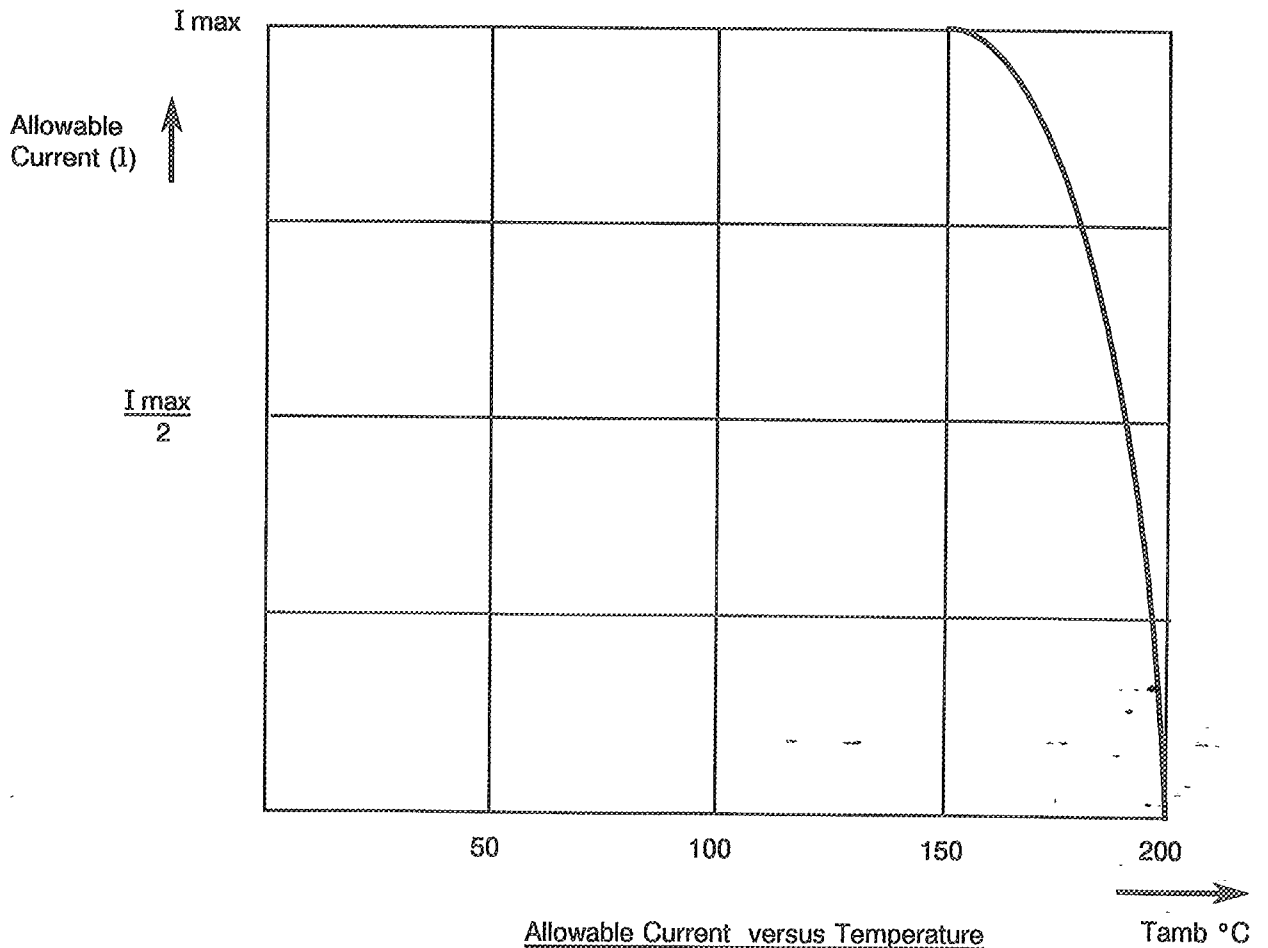

**FIGURE 2 - PHYSICAL CHARACTERISTICS**

Dimensions are given in Table 1(a)

**FIGURE 2(a) - FINISHED WIRES**

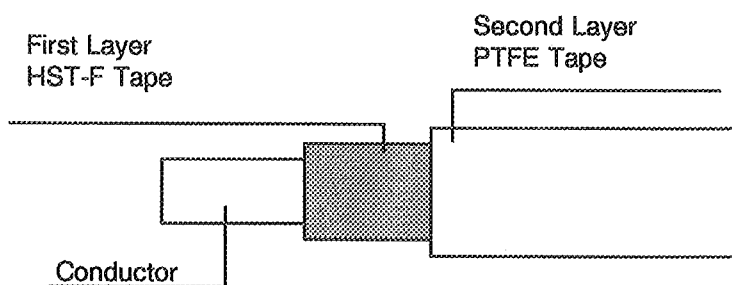


**FIGURE 2(b) - MULTICORE CABLE**




**NOTES**

1. Finished wire according to Figure 2(a).

**FIGURE 2(c) - SHIELDED AND JACKETED CABLES**

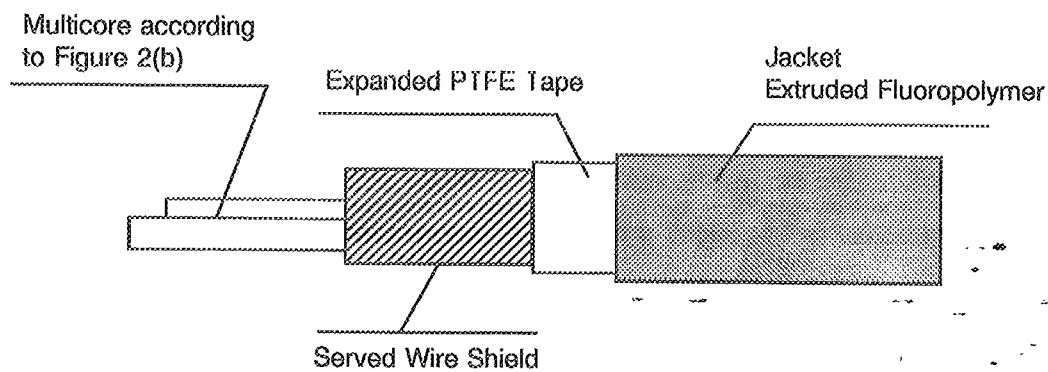

	<p style="text-align: center;">ESA/SCC Detail Specification No. 3901/024</p>	<p style="text-align: right;">PAGE 12 ISSUE 1</p>
--	--	---

3. TERMS, DEFINITIONS, ABBREVIATIONS, SYMBOLS AND UNITS

For the purpose of this specification, the terms, definitions, abbreviations, symbols and units specified in ESA/SCC Basic Specification No. 21300 and ESA/SCC Generic Specification No. 3901 shall apply.

4. REQUIREMENTS

4.1 GENERAL

The complete requirements for procurement of the finished wires and cables specified herein are stated in this specification and ESA/SCC Generic Specification No. 3901. Deviations from the Generic Specification, applicable to this specification only, are listed in Para 4.2.

Deviations from the applicable Generic Specification and this Detail Specification, formally agreed with specific Manufacturers on the basis that the alternative requirements are equivalent to the ESA/SCC requirements and do not affect the components' reliability, are listed in the Appendices attached to this specification.

4.2 DEVIATIONS FROM GENERIC SPECIFICATION

4.2.1 Deviations from Special In-process Controls

None.

4.2.2 Deviations from Final Production Tests (Chart II)

None.

4.2.3 Deviations from Burn-in Tests (Chart III)

Not applicable.

4.2.4 Deviations from Qualification Tests (Chart IV)

None.

4.2.5 Deviations from Lot Acceptance Tests (Chart V)

None.

**4.3 MECHANICAL REQUIREMENTS****4.3.1 Dimension Check**

The dimensions of the finished wires and cables specified herein shall be checked; they shall conform to those shown in Table 1(a), Figure 2 and Para 4.4 of this specification (see below for the list of parameters to be checked).

**LIST OF PARAMETERS TO BE CHECKED**



PARAMETER	TABLE 1(a)	FIGURE 2	PARA 4.4
<b><u>COMPOSITION</u></b>			
Number of conductors	X		
Gauge	X		
Shielding	X		
Jacket		X	
<b><u>CONDUCTOR</u></b>			
Nature			X
Outer diameter	X		
Number of strands	X		
Strand diameter	X		
Length of lay			X
Silver Thickness			X
<b><u>INSULATION</u></b>			
Composition		X	X
Outer diameter	X		
<b><u>SHIELDING</u></b>			
Number of strands	X		
Type of shielding			X
Strand diameter	X		
Nature		X	X
Silver Thickness			X
Shielding lay			X
Shield coverage			X
<b><u>JACKET</u></b>			
Composition		X	X
Protective tape wraps		X	X
Outer diameter	X		

**4.3.2 Weight**

The maximum weight of the finished wires and cables specified herein shall be as specified in Table 1(a).

**4.4 MATERIALS AND FINISHES**

The materials and finishes shall be as specified herein. Where a definite material is not specified, a material which will enable the wires and cables specified herein to meet the performance requirements of this specification shall be used. Acceptance or approval of any constituent material does not guarantee acceptance of the finished product.

		<p style="text-align: center;">ESA/SCC Detail Specification No. 3901/024</p>	<p style="text-align: right;">PAGE 14 ISSUE 1</p>
--	--	--	---

4.4.1 Conductor

4.4.1.1 Material Characteristics

All strands used in the manufacture of the conductors shall be silver-coated, soft or annealed, oxygen-free high conductivity copper for ISO 004, 006, 012 and 030 and silver-coated high strength copper alloy for ISO 001, 002 and AWG 28 and 30.

The silver thickness shall be 2.0 microns minimum.

For all copper conductors, any strand shall show a 10% minimum elongation.

For high-strength copper alloy conductors, the tensile characteristics shall be not less than 6% in elongation and 35kg per square mm in tensile strength.

For determination of the conductor resistance at +20°C, as mentioned in Para 9.5 of ESA/SCC Generic Specification No. 3901, the  $\alpha$  coefficient for copper alloy is 0.0035.

4.4.1.2 Stranding

The conductors shall be constructed of concentrically laid strands to produce a smooth and uniform conductor of circular cross-section and free from any high strands or other surface irregularities.

The length of lay of the external layer shall not be less than 8, nor more than 16, times the maximum conductor diameter specified in Table 1(a).

4.4.2 Insulation

4.4.2.1 Material

Any insulating material shall be virgin high strength toughened fluoropolymer and PTFE with only those additives that are necessary for processing and pigmentation.

4.4.2.2 Construction

The insulation shall have a uniform cross-section throughout the length of the wire and the conductor shall be evenly centred in the insulation.

The insulation shall consist of one wrapped lay of HST-F tapes (min. 76% overlap, wall thickness 0.1 mm nom.) and one lay of PTFE tapes (min. 51% overlap, wall thickness 0.05 mm nom.) as specified in Figure 2(a).

4.4.3 Shield

4.4.3.1 Material Characteristics

Shield strands shall meet the requirements for silver-coated annealed copper outlined in Para. 4.4.1.1 of this specification.

4.4.3.2 Construction

The shield shall be closely and helically wound around the single insulated wire or twisted bundle of insulated wires (core) and provide not less than 90% coverage as calculated by the following formula:

$$K = \frac{n \times d_w \sqrt{(\pi D)^2 + P^2}}{P \pi D} \times 100(\%)$$

- K = Coverage (%).
- n = Number of serving wires.
- $d_w$  = Shield strand diameter (mm).
- D = Diameter of core (mm).
- P = Serving Pitch (mm).



4.4.4 Jacket

All shielded cables shall be provided with jackets of wrapped expanded, microporous polyterafluorethylene tapes and an extruded fluoropolymer (wall thickness 0.2 mm nom.) as specified in Figure 2(c).

4.4.5 Construction of Multicore Cables

Multicore cables shall be constructed by twisting the required number and size of finished wires to form a uniform cable without high strands, bends or other irregularities. Finished wires of only one size shall be used for one cable. The cabling shall be with a left-hand lay and the lay length shall not be less than 12 times and not be more than 16 times the outside diameter of the unshielded jacketed cable. The construction of shielded and jacketed cables is shown in Figure 2(c).

4.4.6 Colour Coding

4.4.6.1 Finished Wire Colour Coding

The colour of the finished wires shall be the red except when colouring is specifically required in the contract.

Colours:

- Black, brown, red, orange, yellow, green, blue, violet, grey, white.

4.4.6.2 Multicore Cable Colour Coding

If the contract does not define any specific colour-coding, all individual cores in multicore cables shall be coloured according to the following scheme.

No. OF CORES IN CABLE	COLOUR OF RESPECTIVE CORES			
2	red	blue		
3	red	blue	yellow	
4	red	blue	yellow	green

4.4.6.3 Jacket colour

The colour of jackets shall be white.

4.5 MARKING


4.5.1 General

The marking of all spools of finished wires and cables delivered to this specification shall be in accordance with the requirements of ESA/SCC Basic Specification No. 21700. Each spool shall be marked in respect of:-

- (a) The SCC Component Number.
- (b) Characteristics.
- (c) Traceability Information.
- (d) Additional Marking.

**4.5.2 The SCC Component Number**

Each spool shall bear the SCC Component Number which shall be constituted and marked as follows:-

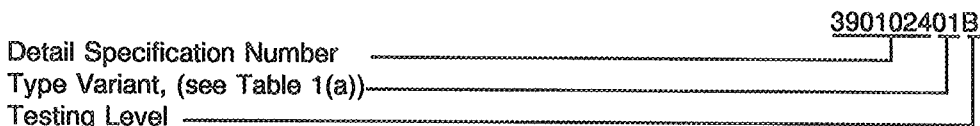

**4.5.3 Characteristics**

The characteristics shall show the length(s) of the finished wire or cable wound on each spool and shall be marked as follows:-



**NOTES**

1. Whenever the length is less than 100 metres, insert a zero in the first block (example: 075 m). If more than one length of finished wire or cable is wound on a spool, the characteristics of each length shall be marked as above.

**4.5.4 Traceability Information**

Each spool shall be marked in respect of traceability information in accordance with the requirements of ESA/SCC Basic Specification No. 21700.

**4.5.5 Additional Marking**

Each spool shall bear the Manufacturer's Quality Control Inspector's stamp.

**4.6 ELECTRICAL MEASUREMENTS**

**4.6.1 Electrical Measurements at Room Temperature**

The parameters to be measured at room temperature are scheduled in Table 2. The measurements shall be performed at  $T_{amb} = +22 \pm 3 \text{ }^\circ\text{C}$ .

**4.6.2 Electrical Measurements at High and Low Temperatures**

Not applicable.

**4.6.3 Circuits for Electrical Measurements**

Not applicable.

**4.7 BURN-IN TESTS**

Not applicable.

**4.8 ENVIRONMENTAL AND ENDURANCE TESTS**

**4.8.1 Mechanical Properties of Conductor**

As detailed in Para. 4.4.1.1 of this specification.

**4.8.2 Accelerated Ageing**

Ageing Temperature  $+230 \pm 5 \text{ }^\circ\text{C}$ .

**4.8.3 Wrap Test at Ambient Temperature**

The mandrel diameters and applied loads for wrap testing of finished wires are given in Table A. The mandrel diameters and applied loads for shielded and jacketed cables are given in Table B.

**TABLE A - MANDREL DIAMETERS AND LOADS FOR FINISHED WIRES**

Wire Size ISO/AWG	Mandrel Diameter (mm)	Applied Weight (kg)
-/30	5.0	0.15
-/28	6.0	0.25
001/26	6.0	0.25
002/24	6.0	0.25
004/22	6.0	0.4
006/20	6.0	0.4
012/16	10	0.5
030/12	20	1.0

**TABLE B - MANDREL DIAMETERS AND LOADS FOR SHIELDED AND JACKETED CABLES**

CABLE SIZE ISO/AWG	NUMBER OF CORES	MANDREL DIAMETER (mm)	APPLIED WEIGHT (kg)
-/30	1	8.0	0.15
-/28	1	8.0	0.25
001/26	1	10	0.25
002/24	1	12	0.25
004/22	1	15	0.5
006/20	1	15	0.5
012/16	1	20	1.0
030/12	1	20	1.0
-/30	2	10	0.25
-/28	2	10	0.5
001/26	2	15	0.5
002/24	2	15	0.5
004/22	2	20	0.8
006/20	2	20	0.8
012/16	2	25	1.0
030/12	2	30	1.0
-/30	3	12	0.25
-/28	3	12	0.5
001/26	3	15	0.75
002/24	3	15	0.75
004/22	3	20	1.2
006/20	3	20	1.2
012/16	3	30	1.5
030/12	3	40	1.5
-/30	4	15	0.5
-/28	4	15	0.8
001/26	4	15	1.0
002/24	4	20	1.0
004/22	4	20	1.5
006/20	4	25	1.5
012/16	4	30	1.5
030/12	4	40	1.5

**4.8.4 Voltage Test**

No particular conditions are applicable.

**4.8.5 Shrinkage**The shrinkage temperature shall be  $+200 \pm 5 \text{ }^\circ\text{C}$ **4.8.6 Blocking**The blocking temperature shall be  $+230 \pm 5 \text{ }^\circ\text{C}$ .**4.8.7 Cold Bend Test**

The mandrel diameters and loads shall be as specified in Table C.

**TABLE C - MANDREL DIAMETERS AND LOADS FOR FINISHED WIRES OR CORES**

Wire Size ISO/AWG	Mandrel Diameter (mm)	Applied Weight (kg)
- /30	5.0	0.15
- /28	6.0	0.25
001/26	6.0	0.25
002/24	6.0	0.25
004/22	6.0	0.4
006/20	6.0	0.4
012/16	10	0.5
030/12	20	1.0

**4.8.8 Cut-through Resistance**

The mean load measured during 9 tests shall not be less than the relevant value specified below.

Wire	ISO	-	-	001	002	004	006	012	030
Size	AWG	30	28	26	24	22	20	16	12
Cut-through Load (kg)		3.0	3.5	3.5	3.5	6.0	7.0	8.0	8.0

**4.8.9 Notch Resistance**

The depth of notch shall be 0.04mm.

**4.8.10 Resistance to Fluids**

No particular conditions are applicable.

**4.8.11 Surface Resistance**

No particular conditions are applicable.

**4.8.12 Abrasion Resistance**

The weight to be applied to the needle is specified below.

Wire	ISO	-	-	001	002	004	006	012	030
Size	AWG	30	28	26	24	22	20	16	12
Scrape Abrasion (Load in grammes)		380	450	480	550	600	600	700	850

**4.8.13 Soldering**

No particular conditions are applicable.

**4.8.14 Solderability**

No particular conditions are applicable.

**4.8.15 Radiation Resistance**

No particular conditions are applicable.

**4.8.16 Overload Resistance**

No particular conditions are applicable.

**4.8.17 Long-term Ageing Test**

The long-term ageing temperature shall be +200°C.

**4.8.18 Antony and Brown Test**

No particular conditions are applicable.

**TABLE 2 - ELECTRICAL MEASUREMENTS AT ROOM TEMPERATURE**

NO	CHARACTERISTICS	SPECIFICATION AND TEST METHOD	TEST CONDITION	LIMITS	UNIT
1	Conductor Resistance	ESA/SCC No. 3901, Section 9	Para 9.5	Table 1(a)	Ω/km
2	Spark Test	ESA/SCC No. 3901, Section 9	Para 9.6	Insulation :3.0 Jacket :1.5	kV
3	Voltage Test	ESA/SCC No. 3901, Section 9	Para 9.7	Para 9.7	kV
4	Insulation Resistance	ESA/SCC No. 3901, Section 9	Para 9.8	Insulation :750 Jacket : 30	MΩ.km
5	Surface Resistance	ESA/SCC No. 3901, Section 9	Para 9.22	125	MΩ.mm

APPENDIX 'A'

AGREED DEVIATIONS FOR GORE (D)

ITEMS AFFECTED	DESCRIPTION OF DEVIATIONS
Figure 2	Expanded PTFE tape shall be GORE-TEX®
Para. 4.4.4	Expanded PTFE tape shall be GORE-TEX®

NOTES

1. GORE-TEX® = Registered Trade Mark of W.L. Gore & Associates GmbH.