

Page 1 of 24

DIODES, MICROWAVE, SILICON, HYPER-ABRUPT JUNCTION TUNING VARACTOR

BASED ON TYPES DH76XXX AND EH76XXX

ESCC Detail Specification No. 5512/023

Issue 6 September 2018



Document Custodian: European Space Agency - see https://escies.org



LEGAL DISCLAIMER AND COPYRIGHT

European Space Agency, Copyright © 2018. All rights reserved.

The European Space Agency disclaims any liability or responsibility, to any person or entity, with respect to any loss or damage caused, or alleged to be caused, directly or indirectly by the use and application of this ESCC publication.

This publication, without the prior permission of the European Space Agency and provided that it is not used for a commercial purpose, may be:

- copied in whole, in any medium, without alteration or modification.
- copied in part, in any medium, provided that the ESCC document identification, comprising the ESCC symbol, document number and document issue, is removed.

No. 5512/023

PAGE 3

ISSUE 6

DOCUMENTATION CHANGE NOTICE

(Refer to https://escies.org for ESCC DCR content)

DCR No.	CHANGE DESCRIPTION
1171	Specification upissued to incorporate changes per DCR.



ESCC Detail Specification

No. 5512/023

PAGE 4

ISSUE 6

TABLE OF CONTENTS

GENERAL	6
SCOPE	6
APPLICABLE DOCUMENTS	6
TERMS, DEFINITIONS, ABBREVIATIONS, SYMBOLS AND UNITS	6
THE ESCC COMPONENT NUMBER AND COMPONENT TYPE VARIANTS	6
The ESCC Component Number	6
Component Type Variants	6
MAXIMUM RATINGS	9
HANDLING PRECAUTIONS	10
PHYSICAL DIMENSIONS AND TERMINAL IDENTIFICATION	10
Ceramic Pill A (2 Leads) - Variants 01, 10, 19, 28, 37, 46, 55, 64	10
Ceramic Pill B - Variants 02, 11, 20, 29, 38, 47, 56, 65	11
Ceramic Pill C (Cathode Lead) - Variants 03, 12, 21, 30, 39, 48, 57, 66	12
Ceramic Pill D (Anode Lead) - Variants 04, 13, 22, 31, 40, 49, 58, 67	13
Ceramic Pill E (2 Leads) - Variants 05, 14, 23, 32, 41, 50, 59, 68	14
Ceramic Pill F (Anode Lead) - Variants 06, 15, 24, 33, 42, 51, 60, 69	15
Ceramic Pill G - Variants 07, 16, 25, 34, 43, 52, 61, 70	16
Ceramic Pill H - Variants 08, 17, 26, 35, 44, 53, 62, 71	17
Ceramic Pill I (2 Leads) - Variants 09, 18, 27, 36, 45, 54, 63, 72	18
Die - Variants 73 to 80	19
FUNCTIONAL DIAGRAM	19
MATERIALS AND FINISHES	20
Materials and Finishes of Packaged Components	20
Materials and Finishes of Die Components	20
REQUIREMENTS	20
GENERAL	20
Deviations from the Generic Specification	20
Deviations from Qualification and Periodic Tests – Chart F4	20
MARKING	20
DIE SHEAR	20
TERMINAL STRENGTH	21
ELECTRICAL MEASUREMENTS AT ROOM, HIGH AND LOW TEMPERATURES	21
Room Temperature Electrical Measurements	21
High and Low Temperatures Electrical Measurements	22
PARAMETER DRIFT VALUES	22
INTERMEDIATE AND END-POINT ELECTRICAL MEASUREMENTS	23
	APPLICABLE DOCUMENTS TERMS, DEFINITIONS, ABBREVIATIONS, SYMBOLS AND UNITS THE ESCC COMPONENT NUMBER AND COMPONENT TYPE VARIANTS THE ESCC COMPONENT NUMBER AND COMPONENT TYPE VARIANTS The ESCC Component Number Component Type Variants MAXIMUM RATINGS HANDLING PRECAUTIONS PHYSICAL DIMENSIONS AND TERMINAL IDENTIFICATION Ceramic Pill A (2 Leads) - Variants 01, 10, 19, 28, 37, 46, 55, 64 Ceramic Pill B - Variants 02, 11, 20, 29, 38, 47, 56, 65 Ceramic Pill C (Cathode Lead) - Variants 03, 12, 21, 30, 39, 48, 57, 66 Ceramic Pill C (Anode Lead) - Variants 04, 13, 22, 31, 40, 49, 58, 67 Ceramic Pill E (2 Leads) - Variants 05, 14, 23, 32, 41, 50, 59, 68 Ceramic Pill F (Anode Lead) - Variants 06, 15, 24, 33, 42, 51, 60, 69 Ceramic Pill G - Variants 07, 16, 25, 34, 43, 52, 61, 70 Ceramic Pill I (2 Leads) - Variants 09, 18, 27, 36, 45, 54, 63, 72 Die - Variants 73 to 80 FUNCTIONAL DIAGRAM MATERIALS AND FINISHES Materials and Finishes of Packaged Components Materials and Finishes of Die Components REQUIREMENTS GENERAL Deviations from the Generic Specification Deviations from Qualification and Periodic Tests – Chart F4 MARKING DIE SHEAR TERMINAL STRENGTH ELECTRICAL MEASUREMENTS AT ROOM, HIGH AND LOW TEMPERATURES Room Temperature Electrical Measurements High and Low Temperatures Electrical Measurements High and Low Temperatures Electrical Measurements



ESCC Detail Specification	PAGE 5
No. 5512/023	ISSUE 6

2.8	BURN-IN 1 CONDITIONS	23
2.9	BURN-IN 2 CONDITIONS	23
2.10	OPERATING LIFE CONDITIONS	23
APPENDIX	'A'	24



1 **GENERAL**

1.1 SCOPE

This specification details the ratings, physical and electrical characteristics and test and inspection data for the component type variants and/or the range of components specified below. It supplements the requirements of, and shall be read in conjunction with, the ESCC Generic Specification listed under Applicable Documents.

1.2 APPLICABLE DOCUMENTS

The following documents form part of this specification and shall be read in conjunction with it:

- (a) ESCC Generic Specification No. 5010
- (b) MIL-STD-750, Test Methods and Procedures for Semiconductor Devices

1.3 TERMS, DEFINITIONS, ABBREVIATIONS, SYMBOLS AND UNITS

For the purpose of this specification, the terms, definitions, abbreviations, symbols and units specified in ESCC Basic Specification No. 21300 shall apply.

1.4 THE ESCC COMPONENT NUMBER AND COMPONENT TYPE VARIANTS

1.4.1 The ESCC Component Number

The ESCC Component Number shall be constituted as follows:

Example: 551202301

Detail Specification Reference: 5512023

• Component Type Variant Number: 01 (as required)

1.4.2 Component Type Variants

The component type variants applicable to this specification are as follows:

Packaged Components

Variant Number	Based On Type	Package Type / Description	Total Capacitance C⊤ (pF)		Tuning Ratio		Lead/Terminal Material and Finish (Note 1)		Weight Max (g)
			Min	Max	Min	Max	Anode	Cathode	
01	DH76010	Ceramic Pill A (2 Leads)	0.9	1.34	3.8	5.1	E2	E2	0.02
02	DH76010	Ceramic Pill B	0.9	1.34	3.8	5.1	D7	D7	0.02
03	DH76010	Ceramic Pill C (Cathode Lead)	0.9	1.34	3.8	5.1	D7	E2	0.02
04	DH76010	Ceramic Pill D (Anode Lead)	0.9	1.34	3.8	5.1	E2	D7	0.02
05	DH76010	Ceramic Pill E (2 Leads)	0.9	1.34	3.8	5.1	E2	E2	0.02
06	DH76010	Ceramic Pill F (Anode Lead)	0.9	1.34	3.8	5.1	E2	D7	0.02
07	DH76010	Ceramic Pill G	0.94	1.42	3.5	4.7	D7	A7	0.15
08	DH76010	Ceramic Pill H	1	1.5	3.3	4.4	D7	D7	0.06
09	DH76010	Ceramic Pill I (2 Leads)	1	1.5	3.3	4.4	E2	E2	0.06
10	DH76015	Ceramic Pill A (2 Leads)	1.3	1.94	4.1	5.5	E2	E2	0.02





Variant Number	Based On Type			itance	Tuning Ratio C _{T1} /C _{T12}		Lead/Terminal Material and Finish (Note 1)		Weight Max (g)
			Min	Max	Min	Max	Anode	Cathode	
11	DH76015	Ceramic Pill B	1.3	1.94	4.1	5.5	D7	D7	0.02
12	DH76015	Ceramic Pill C (Cathode Lead)	1.3	1.94	4.1	5.5	D7	E2	0.02
13	DH76015	Ceramic Pill D (Anode Lead)	1.3	1.94	4.1	5.5	E2	D7	0.02
14	DH76015	Ceramic Pill E (2 Leads)	1.3	1.94	4.1	5.5	E2	E2	0.02
15	DH76015	Ceramic Pill F (Anode Lead)	1.3	1.94	4.1	5.5	E2	D7	0.02
16	DH76015	Ceramic Pill G	1.34	2.02	3.9	5.2	D7	A7	0.15
17	DH76015	Ceramic Pill H	1.4	2.1	3.7	4.9	D7	D7	0.06
18	DH76015	Ceramic Pill I (2 Leads)	1.4	2.1	3.7	4.9	E2	E2	0.06
19	DH76022	Ceramic Pill A (2 Leads)	1.86	2.78	4.3	5.7	E2	E2	0.02
20	DH76022	Ceramic Pill B	1.86	2.78	4.3	5.7	D7	D7	0.02
21	DH76022	Ceramic Pill C (Cathode Lead)	1.86	2.78	4.3	5.7	D7	E2	0.02
22	DH76022	Ceramic Pill D (Anode Lead)	1.86	2.78	4.3	5.7	E2	D7	0.02
23	DH76022	Ceramic Pill E (2 Leads)	1.86	2.78	4.3	5.7	E2	E2	0.02
24	DH76022	Ceramic Pill F (Anode Lead)	1.86	2.78	4.3	5.7	E2	D7	0.02
25	DH76022	Ceramic Pill G	1.9	2.86	4.1	5.5	D7	A7	0.15
26	DH76022	Ceramic Pill H	1.96	2.94	3.9	5.3	D7	D7	0.06
27	DH76022	Ceramic Pill I (2 Leads)	1.96	2.94	3.9	5.3	E2	E2	0.06
28	DH76033	Ceramic Pill A (2 Leads)	2.74	4.1	4.5	6	E2	E2	0.02
29	DH76033	Ceramic Pill B	2.74	4.1	4.5	6	D7	D7	0.02
30	DH76033	Ceramic Pill C (Cathode Lead)	2.74	4.1	4.5	6	D7	E2	0.02
31	DH76033	Ceramic Pill D (Anode Lead)	2.74	4.1	4.5	6	E2	D7	0.02
32	DH76033	Ceramic Pill E (2 Leads)	2.74	4.1	4.5	6	E2	E2	0.02
33	DH76033	Ceramic Pill F (Anode Lead)	2.74	4.1	4.5	6	E2	D7	0.02
34	DH76033	Ceramic Pill G	2.74	4.18	4.3	5.8	D7	A7	0.15
35	DH76033	Ceramic Pill H	2.84	4.26	4.2	5.6	D7	D7	0.06
36	DH76033	Ceramic Pill I (2 Leads)	2.84	4.26	4.2	5.6	E2	E2	0.06
37	DH76047	Ceramic Pill A (2 Leads)	3.86	5.78	4.6	6.1	E2	E2	0.02
38	DH76047	Ceramic Pill B	3.86	5.78	4.6	6.1	D7	D7	0.02
39	DH76047	Ceramic Pill C (Cathode Lead)	3.86	5.78	4.6	6.1	D7	E2	0.02
40	DH76047	Ceramic Pill D (Anode Lead)	3.86	5.78	4.6	6.1	E2	D7	0.02
41	DH76047	Ceramic Pill E (2 Leads)	3.86	5.78	4.6	6.1	E2	E2	0.02
42	DH76047	Ceramic Pill F (Anode Lead)	3.86	5.78	4.6	6.1	E2	D7	0.02
43	DH76047	Ceramic Pill G	3.9	5.86	4.5	6	D7	A7	0.15
44	DH76047	Ceramic Pill H	3.96	5.94	4.4	5.8	D7	D7	0.06
45	DH76047	Ceramic Pill I (2 Leads)	3.96	5.94	4.4	5.8	E2	E2	0.06



PAGE 8

No. 5512/023



ISSUE 6

Variant Number	Based On Type	9 7.		tal itance (pF)		g Ratio C _{T12}	Mater	erminal ial and (Note 1)	Weight Max (g)
			Min	Max	Min	Max	Anode	Cathode	
46	DH76068	Ceramic Pill A (2 Leads)	5.54	8.3	4.6	6.2	E2	E2	0.02
47	DH76068	Ceramic Pill B	5.54	8.3	4.6	6.2	D7	D7	0.02
48	DH76068	Ceramic Pill C (Cathode Lead)	5.54	8.3	4.6	6.2	D7	E2	0.02
49	DH76068	Ceramic Pill D (Anode Lead)	5.54	8.3	4.6	6.2	E2	D7	0.02
50	DH76068	Ceramic Pill E (2 Leads)	5.54	8.3	4.6	6.2	E2	E2	0.02
51	DH76068	Ceramic Pill F (Anode Lead)	5.54	8.3	4.6	6.2	E2	D7	0.02
52	DH76068	Ceramic Pill G	5.58	8.38	4.6	6.1	D7	A7	0.15
53	DH76068	Ceramic Pill H	5.64	8.46	4.5	6	D7	D7	0.06
54	DH76068	Ceramic Pill I (2 Leads)	5.64	8.46	4.5	6	E2	E2	0.06
55	DH76100	Ceramic Pill A (2 Leads)	8.1	12.14	4.7	6.3	E2	E2	0.02
56	DH76100	Ceramic Pill B	8.1	12.14	4.7	6.3	D7	D7	0.02
57	DH76100	Ceramic Pill C (Cathode Lead)	8.1	12.14	4.7	6.3	D7	E2	0.02
58	DH76100	Ceramic Pill D (Anode Lead)	8.1	12.14	4.7	6.3	E2	D7	0.02
59	DH76100	Ceramic Pill E (2 Leads)	8.1	12.14	4.7	6.3	E2	E2	0.02
60	DH76100	Ceramic Pill F (Anode Lead)	8.1	12.14	4.7	6.3	E2	D7	0.02
61	DH76100	Ceramic Pill G	8.14	12.22	4.2	6.2	D7	A7	0.15
62	DH76100	Ceramic Pill H	8.2	12.3	4.6	6.1	D7	D7	0.06
63	DH76100	Ceramic Pill I (2 Leads)	8.2	12.3	4.6	6.1	E2	E2	0.06
64	DH76150	Ceramic Pill A (2 Leads)	12.1	18.14	4.7	6.3	E2	E2	0.02
65	DH76150	Ceramic Pill B	12.1	18.14	4.7	6.3	D7	D7	0.02
66	DH76150	Ceramic Pill C (Cathode Lead)	12.1	18.14	4.7	6.3	D7	E2	0.02
67	DH76150	Ceramic Pill D (Anode Lead)	12.1	18.14	4.7	6.3	E2	D7	0.02
68	DH76150	Ceramic Pill E (2 Leads)	12.1	18.14	4.7	6.3	E2	E2	0.02
69	DH76150	Ceramic Pill F (Anode Lead)	12.1	18.14	4.7	6.3	E2	D7	0.02
70	DH76150	Ceramic Pill G	12.1	18.22	4.7	6.3	D7	A7	0.15
71	DH76150	Ceramic Pill H	12.2	18.3	4.7	6.2	D7	D7	0.06
72	DH76150	Ceramic Pill I (2 Leads)	12.2	18.3	4.7	6.2	E2	E2	0.06



Die Components (Note 2)

Variant Number	Based On Type	Junction Capacitance C _J (pF)		Tuning Ratio		Capac C _T	otal citance (pF) te 3)	C _{T1} /	Ratio C _{T12} :e 3)
		Min	Max	Min	Max	Min	Max	Min	Max
73	EH76010	0.8	1.2	4.6	6.1	0.94	1.42	3.5	4.7
74	EH76015	1.2	1.8	4.7	6.3	1.34	2.02	3.9	5.2
75	EH76022	1.76	2.64	4.7	6.3	1.9	2.86	4.1	5.5
76	EH76033	2.64	3.96	4.8	6.4	2.74	4.18	4.3	5.8
77	EH76047	3.76	5.64	4.8	6.4	3.9	5.86	4.5	6
78	EH76068	5.44	8.16	4.8	6.4	5.58	8.38	4.6	6.1
79	EH76100	8	12	4.8	6.4	8.14	12.22	4.2	6.2
80	EH76150	12	18	4.8	6.4	12.1	18.22	4.7	6.3

<u>NOTES:</u>

- The lead/terminal material and finish shall be in accordance with the requirements of ESCC Basic Specification No. 23500.
- 2. For Die Components, Variants 73 to 80, the default package selected for assembly of the Packaged Test Sublot shall be Ceramic Pill G. At the Manufacturer's option, any of the other packages specified herein with a Variant for the same die may be selected. The die applicable to each Variant is indicated by the based on type number.
- 3. In cases where the default package is not selected for the Packaged Test Sublot, the Total Capacitance and Tuning Ratio limits of the selected package shall apply.

1.5 <u>MAXIMUM RATINGS</u>

The maximum ratings shall not be exceeded at any time during use or storage.

Maximum ratings shall only be exceeded during testing to the extent specified in this specification and when stipulated in Test Methods and Procedures of the ESCC Generic Specification.

Characteristics	Symbols	Maximum Ratings	Unit	Remarks
Reverse Voltage	V_{Rmax}	-20	V	I _R = 10μA Note 1
Operating Temperature Range	Тор	-55 to +150	°C	T _{amb}
Storage Temperature Range	T _{stg}	-65 to +175	°C	
Soldering Temperature	T _{sol}	+230	°C	Note 2

NOTES:

- 1. At $T_{amb} \le +25$ °C. For $T_{amb} > +25$ °C, derate linearly to -16V at $T_{amb} = +150$ °C.
- 2. Duration 5 seconds maximum and the same terminal shall not be resoldered until 3 minutes have elapsed. Only applicable to Variants 01 to 72 (Packaged Components).



1.6 HANDLING PRECAUTIONS


These devices are susceptible to damage by electrostatic discharge. Therefore, suitable precautions shall be employed for protection during all phases of manufacture, testing, packaging, shipment and any handling.

Variants 01 to 45, 55 to 77, 79 and 80 are categorised as Class 2 per ESCC Basic Specification No. 23800 with a Minimum Critical Path Failure Voltage of 2500V.

Variants 46 to 54 and 78 are categorised as Class 3 per ESCC Basic Specification No. 23800 with a Minimum Critical Path Failure Voltage of 5000V.

1.7 PHYSICAL DIMENSIONS AND TERMINAL IDENTIFICATION

1.7.1 <u>Ceramic Pill A (2 Leads) - Variants 01, 10, 19, 28, 37, 46, 55, 64</u>

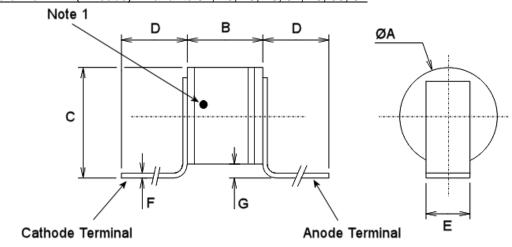


Cumbala	Dimensi	Domorko	
Symbols	Min	Max	Remarks
ØA	1.07	1.47	
В	0.95	1.35	
С	1.3	1.9	Both terminals
D	2.5	-	
E	0.55	0.65	Both terminals
F	0.06	0.1	Both terminals
G	0.1	0.5	Both terminals

NOTES:

 Terminal identification: The body shall be marked at a suitable location near the cathode terminal with a black dot.



1.7.2 Ceramic Pill B - Variants 02, 11, 20, 29, 38, 47, 56, 65

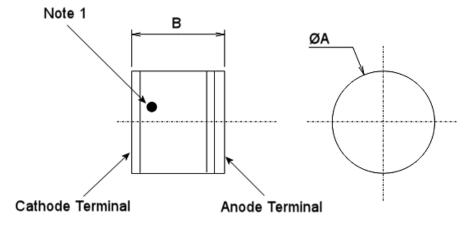


Cumbala	Dimensions mm				
Symbols	Min	Max			
ØA	1.07	1.47			
В	0.95	1.35			

NOTES:

Terminal identification: The body shall be marked at a suitable location near the cathode terminal with a black dot.



1.7.3 <u>Ceramic Pill C (Cathode Lead) - Variants 03, 12, 21, 30, 39, 48, 57, 66</u>

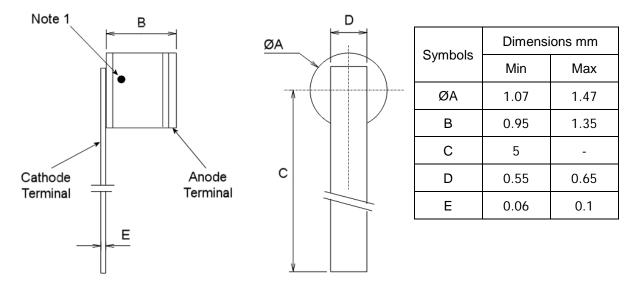


NOTES:

Terminal identification: The body shall be marked at a suitable location near the cathode terminal with a black dot.



ISSUE 6 No. 5512/023

1.7.4 Ceramic Pill D (Anode Lead) - Variants 04, 13, 22, 31, 40, 49, 58, 67

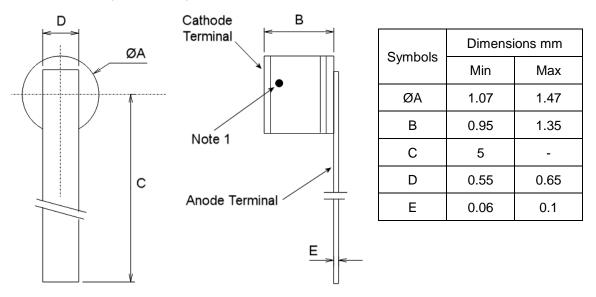


NOTES:

Terminal identification: The body shall be marked at a suitable location near the cathode terminal with a black dot.



1.7.5 Ceramic Pill E (2 Leads) - Variants 05, 14, 23, 32, 41, 50, 59, 68

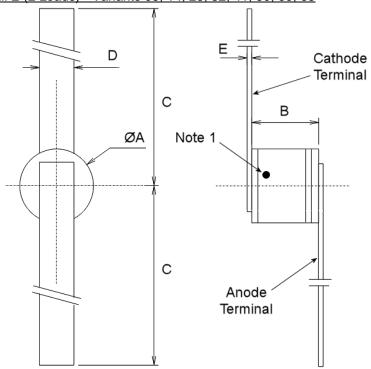


Curre hade	Dimensi	ons mm	Damada
Symbols	Min	Max	Remarks
ØA	1.07	1.47	
В	0.95	1.35	
С	5	1	
D	0.55	0.65	Both terminals
E	0.06	0.1	Both terminals

NOTES:

Terminal identification: The body shall be marked at a suitable location near the cathode terminal with a black dot.



1.7.6 <u>Ceramic Pill F (Anode Lead) - Variants 06, 15, 24, 33, 42, 51, 60, 69</u>

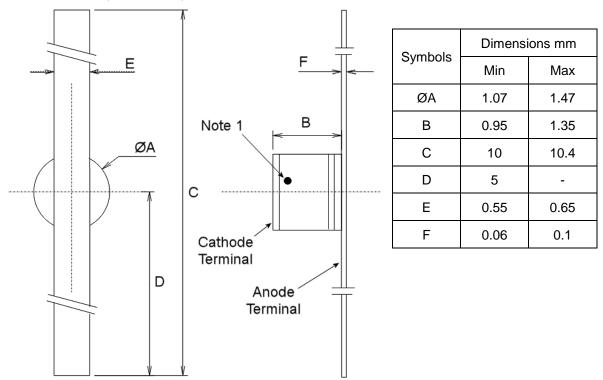


NOTES:

1. Terminal identification: The body shall be marked at a suitable location near the cathode terminal with a black dot.



1.7.7 <u>Ceramic Pill G - Variants 07, 16, 25, 34, 43, 52, 61, 70</u>

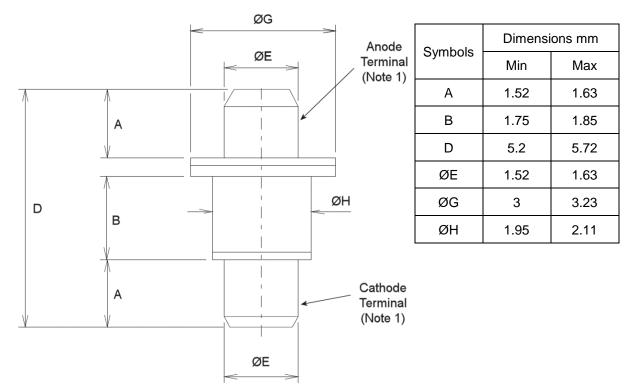


NOTES:

1. Terminal identification shall be by means of the physical configuration of the package.



No. 5512/023

1.7.8 Ceramic Pill H - Variants 08, 17, 26, 35, 44, 53, 62, 71

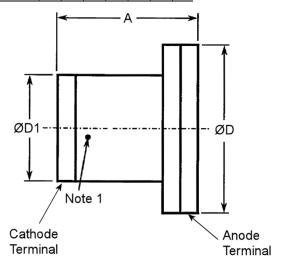

Cumbala	Dimensions mm		
Symbols	Min	Max	
А	1.4	1.6	
ØD	2.94	3.14	
ØD1	1.93	2.13	


NOTES:

1. Terminal identification: The body shall be marked at a suitable location near the cathode terminal with a black dot.



2/023 ISSUE 6

1.7.9 <u>Ceramic Pill I (2 Leads) - Variants 09, 18, 27, 36, 45, 54, 63, 72</u>

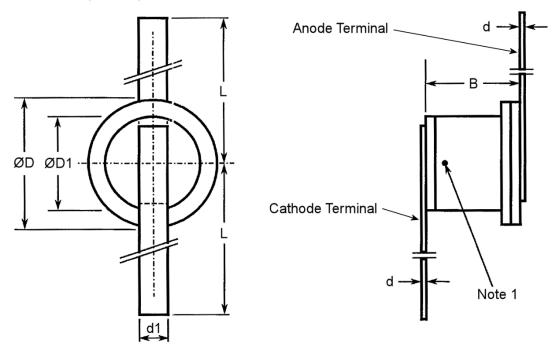


Cymbolo	Dimensi	ons mm	Remarks
Symbols	Min	Max	Remarks
В	1.38	1.73	
d	0.07	0.08	
d1	0.95	1.05	Both terminals
ØD	2.95	3.15	
ØD1	1.93	2.13	
L	9	-	

NOTES:

Terminal identification: The body shall be marked at a suitable location near the cathode terminal with a black dot.

1.7.10 <u>Die - Variants 73 to 80</u>

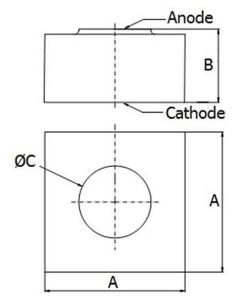

	Dimensi	ions mm	
Symbols	Min	Max	Remarks
А	0.34	0.4	
В	0.16	0.26	
ØC	0.03 0.05 0.07 0.09 0.11 0.13 0.15	0.06 0.08 0.1 0.12 0.14 0.16 0.19	Variant 73 Variant 74 Variant 75 Variant 76 Variant 77 Variant 78 Variant 79
ØC	0.09 0.11 0.13	0.12 0.14 0.16	Variant 76 Variant 77 Variant 78

NOTES:

- 1. Terminal identification shall be by means of the physical configuration.
- 2. Die construction, materials, finishes:
 - Die substrate: Silicon
 - Bond pad: The metallisation shall be TiPtAu with a layer of vacuum-deposited gold of thickness 0.7µm minimum.
 - Die backface: The metallisation shall be TiPtAu with a layer of gold of thickness 0.7μm minimum.
 - Glassivation: Silicon oxide or silicon nitride of thickness 0.25µm typical.

1.8 FUNCTIONAL DIAGRAM



- 1. Anode
- 2. Cathode



1.9 MATERIALS AND FINISHES

1.9.1 Materials and Finishes of Packaged Components

For Variants 01 to 72, the materials and finishes shall be as follows:

- (a) Case
 - The case shall be hermetically sealed and have a ceramic body with a metal base and lid.
- (b) Leads/TerminalsAs specified in Para. 1.4.2.

1.9.2 Materials and Finishes of Die Components

For Variants 73 to 80, the materials and finishes shall be as specified in Para. 1.7.10.

2 **REQUIREMENTS**

2.1 GENERAL

The complete requirements for procurement of the components specified herein are as stated in this specification and the ESCC Generic Specification. Permitted deviations from the Generic Specification, applicable to this specification only, are listed below.

Permitted deviations from the Generic Specification and this Detail Specification, formally agreed with specific Manufacturers on the basis that the alternative requirements are equivalent to the ESCC requirement and do not affect the component's reliability, are listed in the appendices attached to this specification.

2.1.1 <u>Deviations from the Generic Specification</u>

2.1.1.1 Deviations from Qualification and Periodic Tests - Chart F4

- (a) Mechanical Shock: Shall not be performed.
- (b) Vibration: Shall not be performed.
- (c) Constant Acceleration: Shall not be performed.

2.2 MARKING

The marking shall be in accordance with the requirements of ESCC Basic Specification No. 21700 and as follows.

The information to be marked on the component or its primary package shall be:

- (a) Terminal identification, as specified in Para. 1.7.
- (b) The ESCC qualified components symbol (for ESCC qualified components only).
- (c) The ESCC Component Number.
- (d) Traceability information.

2.3 DIE SHEAR

In those cases where package clearances are such that a die shear test is not practicable, the die shall be pushed away with a suitable tool. The force required to remove the die need not be recorded. The die attachment area shall be inspected and the component shall be considered acceptable if more than 50% of the semiconductor material remains.



2.4 TERMINAL STRENGTH

The test conditions for terminal strength, tested as specified in the ESCC Generic Specification, shall be as follows:

- For Variants 01, 03 to 06, 09, 10, 12 to 15, 18, 19, 21 to 24, 27, 28, 30 to 33, 36, 37, 39 to 42, 45, 46, 48 to 51, 54, 55, 57 to 60, 63, 64, 66 to 69, 72: Test Condition A, tension, with a force of 1.25N for duration 10s.
- For Variants 02, 07, 08, 11, 16, 17, 20, 25, 26, 29, 34, 35, 38, 43, 44, 47, 52, 53, 56, 61, 62, 65, 70, 71: shall not be performed.
- For Variants 73 to 80: not applicable.

2.5 ELECTRICAL MEASUREMENTS AT ROOM, HIGH AND LOW TEMPERATURES

2.5.1 Room Temperature Electrical Measurements

The measurements shall be performed at $T_{amb} = +22 \pm 3$ °C.

Characteristics	Symbols	MIL-STD-750	Test Conditions	Lin	nits	Units
		Test Method		Min	Max	
Reverse Current 1 (Note 1)	I _{R1}	4016	V _R = -20V	-	10	μΑ
Reverse Current 2 (Note 1)	I _{R2}	4016	V _R = -16V	-	50	nΑ
Forward Voltage (Note 1)	V _F	4011	I _F = 10mA	-	1	V
Total Capacitance (Note 2)	Ст	4001	$V_R = -4V$, $f = 1MHz$	Note 3	Note 3	pF
Junction Capacitance (Note 4)	С	4001	$V_R = -4V$, $f = 1MHz$	Note 3	Note 3	pF
Tuning Ratio (Notes 2, 5)	C _{T1} /C _{T12}	4001	$V_R = -1V$ and $-12V$ f = 1MHz	Note 3	Note 3	-
Tuning Ratio (Notes 4, 6)	C _{J1} /C _{J12}	4001	$V_R = -1V$ and $-12V$ f = 1MHz	Note 3	Note 3	-
Quality Factor (Note 7)	Q	-	$V_R = -4V$, $f = 1GHz$			-
Variants 01 to 09, 73: Variants 10 to 18, 74: Variants 19 to 27, 75: Variants 28 to 36, 76: Variants 37 to 45, 77: Variants 46 to 54, 78: Variants 55 to 63, 79: Variants 64 to 72, 80:				100 90 75 58 40 25 12 4	- - - - -	

NOTES:

- 1. This characteristic applies to all Variants tested during Charts F2 and F3 of the Generic Specification.
- 2. This characteristic applies to Variants 01 to 72 (Packaged Components) and Variants 73 to 80 (Packaged Test Sublot samples for Die Components), tested only during Chart F3 of the Generic Specification.
- 3. See Para. 1.4.2 for the applicable limits.
- 4. This characteristic applies only to Variants 73 to 80 (Die Components), tested only during Chart F2 of the Generic Specification.



- 5. For Variants 01 to 72 (Packaged Components) and Variants 73 to 80 (Packaged Test Sublot samples for Die Components) tested during Chart F3 of the Generic Specification, the Tuning Ratio is determined by dividing the Total Capacitance at $V_R = -1V$ by the Total Capacitance at $V_R = -12V$.
- 6. For Variants 73 to 80 (Die Components) tested during Chart F2 of the Generic Specification, the Tuning Ratio is determined by dividing the Junction Capacitance at $V_R = -1V$ by the Junction Capacitance at $V_R = -12V$.
- 7. Guaranteed but not tested.

2.5.2 <u>High and Low Temperatures Electrical Measurements</u>

The measurements shall be performed only at $T_{amb} = +150 (+0 -3)$ °C.

Characteristics	Symbols	MIL-STD-750 Test Method	Test Conditions Note 1	Limits		Units
				Min	Max	
Reverse Current 2 (Note 2)	I _{R2}	4016	V _R = -16V	-	10	μΑ

NOTES:

- Measurements shall be performed on a sample basis as specified in the Generic Specification.
- This characteristic applies to all Variants tested during Charts F2 and F3 of the Generic Specification.

2.6 PARAMETER DRIFT VALUES

Unless otherwise specified, the measurements shall be performed at T_{amb} = +22 ±3°C.

The test methods and test conditions shall be as per the corresponding test defined in Para. 2.5.1, Room Temperature Electrical Measurements.

The drift values (Δ) shall not be exceeded for each characteristic specified. The corresponding absolute limit values for each characteristic shall not be exceeded.

Characteristics	Symbols	Limits			Units
		Drift			
		Value (1) Δ	Min	Max	
Reverse Current 2	I _{R2}	±10 or (2) ±100%	-	50	nA
Forward Voltage	VF	±5%	-	1	V
Total Capacitance (Note 3)	Ст	±5%	Note 4	Note 4	pF

NOTES:

- 1. $\Delta 1 = \Delta 2$.
- 2. Whichever is the greater referred to the initial value.
- 3. This characteristic applies to Variants 01 to 72 (Packaged Components) and Variants 73 to 80 (Packaged Test Sublot samples for Die Components).
- 4. See Para. 1.4.2 for the applicable limits.



2.7 <u>INTERMEDIATE AND END-POINT ELECTRICAL MEASUREMENTS</u>

Unless otherwise specified, the measurements shall be performed at T_{amb} = +22 ±3°C.

The test methods and test conditions shall be as per the corresponding test defined in Para. 2.5.1, Room Temperature Electrical Measurements.

The limit values for each characteristic shall not be exceeded.

Characteristics	Symbols	Limits		Units
		Min	Max	
Reverse Current 2	I _{R2}	-	20	μΑ
Forward Voltage	VF	-	1	V
Total Capacitance (Note 1)	Ст	Note 2	Note 2	pF

NOTES:

- This characteristic applies to Variants 01 to 72 (Packaged Components) and Variants 73 to 80 (Packaged Test Sublot samples for Die Components).
- 2. See Para. 1.4.2 for the applicable limits.

2.8 BURN-IN 1 CONDITIONS

Characteristics	Symbols	Test Conditions	Units
Ambient Temperature	T _{amb}	+125 (+0 -3)	°C
Forward Current	l _F	50	mA

2.9 BURN-IN 2 CONDITIONS

Characteristics	Symbols	Test Conditions	Units
Ambient Temperature	T _{amb}	+150 (+0 -3)	°C
Reverse Voltage	V_{R}	-16	V

2.10 OPERATING LIFE CONDITIONS

The conditions shall be as specified in Para. 2.9.



APPENDIX 'A' AGREED DEVIATIONS FOR COBHAM MICROWAVE (F)

Items Affected	Description of Deviations		
Para. 2.1.1, Deviations from the Generic Specification:	SEM Inspection: SEM inspection shall be performed on three dice from one wafer per metallisation run, selected after die separation.		
Deviations from Special In- Process Controls – Chart F2	Bond Strength: The following pre-seal bond strength shall apply: • 0.03N minimum		
Para. 2.1.1, Deviations from	Radiographic Inspection:		
the Generic Specification: Deviations from Screening Tests for Packaged Components – Chart F3A	 May be performed without serialisation and at any point during Chart F3A. Any components found to fail Radiographic Inspection shall be removed from the lot. May be performed in the X and Z axes only. 		
Para. 2.1.1.1, Deviations from Qualification and Periodic Tests – Chart F4	For the De-encapsulation Subgroup, the Internal Visual Inspection, Bond Strength and Die Shear tests may be replaced by measurements verifying the die solder integrity and wire integrity, as follows:		
	 Thermal Impedance test in accordance with MIL-STD-750, Test Method 3101. 		
	• P _D = 0.25W.		
	The Thermal Impedance shall be measured and shall not exceed 150°C/W.		
	 Forward Voltage test in accordance with MIL-STD-750, Test Method 4011. 		
	• I _F =100mA.		
	The Forward Voltage shall be measured and shall not exceed 1.2V.		