

Page i

# DIODES, MICROWAVE, SILICON, PIN, PLATED HEATSINK, BASED ON TYPES ML4630 AND ML4631 ESCC Detail Specification No. 5513/003

# ISSUE 1 October 2002





#### **ESCC Detail Specification**

PAGE	ii
ISSUE	1

#### **LEGAL DISCLAIMER AND COPYRIGHT**

European Space Agency, Copyright © 2002. All rights reserved.

The European Space Agency disclaims any liability or responsibility, to any person or entity, with respect to any loss or damage caused, or allleged to be caused, directly or indirectly by the use and application of this ESCC publication.

This publication, without the prior permission of the European Space Ageny and provided that it is not used for a commercial purpose, may be:

- copied in whole in any medium without alteration or modification.
- copied in part, in any medium, provided that the ESCC document identification, comprising the ESCC symbol, document number and document issue, is removed.



# european space agency agence spatiale européenne

Pages 1 to 34

# DIODES, MICROWAVE, SILICON, PIN, PLATED HEATSINK, BASED ON TYPES ML4630 AND ML4631 ESA/SCC Detail Specification No. 5513/003



# space components coordination group

		Approved by		
Issue/Rev.	Date	SCCG Chairman	ESA Director General or his Deputy	
Issue 1	November 1992	Pommens	Literty	
Revision 'A'	December 1993	Tomomens	1, lest	
Revision 'B'	April 1994	Pomomical	1 tule	
	·			



Rev. 'B'

PAGE 2

ISSUE 1

# **DOCUMENTATION CHANGE NOTICE**

Rev. Letter	Rev. Date	CHANGE Reference Item	Approved DCR No.
'A'	Dec '93	P1. Cover Page P2. DCN P4. T of C : 'Type Variant' changed to 'Type Variants' P28. Table 2 : Table standardised P29. Table 3 : Table standardised Table 4 : Table standardised P33. Table 6 : Table standardised	None None 23618 23618 23618 23618 23618
'B'	Apr. '94	P1. Cover Page P2. DCN P23. Para. 4.2.4 : Clause on bond strength amended	None None 221039



PAGE 3

ISSUE 1

# TABLE OF CONTENTS

1.	<u>GENERAL</u>	<u>Page</u> <b>5</b>
1.1	Scope	5
1.2	Type Variants	5
1.3	Maximum Ratings	5 5
1.4	Parameter Derating Information	5
1.5	Physical Dimensions	5
1.6	Functional Diagram	5 5
1.7	Handling Precautions	5
2.	APPLICABLE DOCUMENTS	5
3.	TERMS, DEFINITIONS, ABBREVIATIONS, SYMBOLS AND UNITS	5
4.	REQUIREMENTS	23
4.1	General	23
4.2	Deviations from Generic Specification	23
4.2.1	Deviations from Special In-process Controls	23
4.2.2	Deviations from Final Production Tests	23
4.2.3	Deviations from Burn-in and Electrical Measurements	23
4.2.4	Deviations from Qualification Tests	23
4.2.5	Deviations from Lot Acceptance Tests	23
4.3	Mechanical and Environmental Requirements	24
4.3.1	Dimension Check	24
4.3.2	Weight	24
4.3.3	Terminal Strength	24
4.4	Materials and Finishes	25
4.4.1	Case	25
4.4.2	Lead Materials and Finish	25
4.5	Marking	26
4.5.1	General	26
4.5.2	Cathode Identification	26
4.5.3	The SCC Component Number	26
4.5.4	Traceability Information	26
4.6	Electrical Measurements	26
4.6.1	Electrical Measurements at Room Temperature	26
4.6.2	Electrical Measurements at High and Low Temperatures	26
4.6.3	Circuits for Electrical Measurements	26
4.7	Burn-in Tests	27
4.7.1	Parameter Drift Values	27
4.7.2	Conditions for High Temperature Reverse Bias Burn-in	27
4.7.3	Conditions for Power Burn-in	27
4.7.4	Electrical Circuits for High Temperature Reverse Bias and Power Burn-in	27
4.8	Environmental and Endurance Tests	32
4.8.1	Electrical Measurements on Completion of Environmental Tests	32
4.8.2	Electrical Measurements at Intermediate Points and on Completion of Endurance Tests	32
4.8.3	Conditions for Operating Life Tests	32
4.8.4	Electrical Circuits for Operating Life Tests	32
4.9	Total Dose Irradiation Testing	32
4.9.1	Application	32
4.9.2	Bias Conditions	32
4.9.3	Electrical Measurements	32
4.10	Special Testing	32



Rev. 'A'

PAGE 4

ISSUE 1

TABLES	<u>S</u>	<u>Page</u>
1(a)	Type Variants	6
1(b)	Maximum Ratings	7
2	Electrical Measurements at Room Temperature - D.C. Parameters	28
	Electrical Measurements at Room Temperature - A.C. Parameters	28
3	Electrical Measurements at High and Low Temperatures	29
4	Parameter Drift Values	29
5(a)	Conditions for High Temperature Reverse Bias Burn-in	31
<b>5</b> (b)	Conditions for Power Burn-in	31
5(c)	Conditions for Operating Life Tests	31
6	Electrical Measurements at Intermediate Points and on Completion of Endurance Testing	33
7	Electrical Measurements During and on Completion of Irradiation Testing	34
FIGURE	<u>es</u>	
1	Parameter Derating Information	8
2	Physical Dimensions	9
3	Functional Diagram	22
4	Circuits for Electrical Measurements	30
5(a)	Electrical Circuit for High Temperature Reverse Bias Burn-in	31
5(b)	Electrical Circuit for Power Burn-in and Operating Life Tests	31
6	Bias Conditions for Irradiation Testing	33

APPENDICES (Applicable to specific Manufacturers only)

None.



PAGE

5

ISSUE

#### 1. GENERAL

#### 1.1 SCOPE

This specification details the ratings, physical and electrical characteristics, test and inspection data for a Diode, Microwave, Silicon, PIN, Plated Heatsink, based on Types ML4630 and ML4631. It shall be read in conjunction with ESA/SCC Generic Specification No. 5010, the requirements of which are supplemented herein.

#### 1.2 TYPE VARIANTS

Variants of the basic diodes specified herein, which are also covered by this specification are given in Table 1(a).

#### 1.3 MAXIMUM RATINGS

The maximum ratings, which shall not be exceeded at any time during use or storage, applicable to the diodes specified herein, are as scheduled in Table 1(b).

#### 1.4 PARAMETER DERATING INFORMATION

The derating information applicable to the diodes specified herein is shown in Figure 1.

#### 1.5 PHYSICAL DIMENSIONS

The physical dimensions of the diodes specified herein are shown in Figure 2.

#### 1.6 <u>FUNCTIONAL DIAGRAM</u>

The functional diagram, showing lead identification, of the diodes specified herein, is shown in Figure 3.

#### 1.7 HANDLING PRECAUTIONS

These devices are susceptible to damage by electrostatic discharge. Therefore, suitable precautions shall be employed for protection during all phases of manufacture, testing, packaging, shipment and any handling.

These components are Categorised as Class 1 with a Minimum Critical Path Failure Voltage of 1250V.

#### 2. APPLICABLE DOCUMENTS

The following documents form part of this specification and shall be read in conjunction with it:

(a) ESA/SCC Generic Specification No. 5010 for Discrete Microwave Semiconductor Components.

#### 3. TERMS, DEFINITIONS, ABBREVIATIONS, SYMBOLS AND UNITS

For the purpose of this specification, the terms, definitions, abbreviations, symbols and units specified in ESA/SCC Basic Specification No. 21300 shall apply.



PAGE 6

ISSUE 1

# TABLE 1(a) - TYPE VARIANTS

(1) VARIANT	BASED ON	(3) FIGURE	(4) TOTAL CAPACITANCE C <sub>T</sub> (pF)		JUNCTION CAPACITANCE	(6) BODY-LID AND LEAD
	TYPE		MIN	MAX	C <sub>J</sub> (pF) (Typical)	MATERIAL AND FINISH
01	ML4630 - 30	2(a)	0.30	0.50	0.2	A7-D2
02	ML4630 - 31	2(b)	0.30	0.50	0.2	A7-D2
03	ML4630 - 32	2(c)	0.41	0.61	0.2	A7-D2
04	ML4630 - 34	2(d)	0.50	0.70	0.2	A7-D2
05	ML4630 - 36	2(e)	0.30	0.50	0.2	A7-D2
06	ML4630 - 43	2(f)	0.90	1.10	0.2	A7-D2
07	ML4630 - 56	2(g)	0.63	0.83	0.2	A7-D2
08	ML4630 - 91	2(h)	0.41	0.61	0.2	A7-D2
09	ML4630 - 92	2(i)	0.41	0.61	0.2	A7-D2
10	ML4630 - 94	2(j)	0.28	0.48	0.2	A7-D2
11	ML4630 - 95	2(k)	0.28	0.48	0.2	A7-D2
12	ML4630 - 96	2(I)	0.28	0.48	0.2	A7-D2
13	ML4630 - 97	2(m)	0.28	0.48	0.2	A7-D2
14	ML4630 - 101	2(n)	0.60	0.80	0.2	A7-D2
15	ML4630 - 103	2(0)	0.41	0.61	0.2	A7-D2
16	ML4630 - 118	2(p)	0.35	0.55	0.2	<b>A</b> 7
17	ML4630 - 120	2(q)	0.26	0.46	0.2	D2
18	ML4630 - 128	2(r)	0.36	0.56	0.2	A7-D2
19	ML4630 - 138	2(s)	0.31	0.51	0.2	A7
20	ML4630 - 148	2(t)	0.39	0.59	0.2	A7
21	ML4630 - 255	2(u)	0.40	0.60	0.2	A7
22	ML4630 - 275	2(v)	0.48	0.68	0.2	A7
23	ML4630 - 276	2(w)	0.26	0.46	0.2	D2
24	ML4630 - 186	2(x)	0.25	0.45	0.2	D2
25	ML4631 - 30	2(a)	0.40	0.60	0.3	A7-D2
26	ML4631 - 31	2(b)	0.40	0.60	0.3	A7-D2
27	ML4631 - 32	2(c)	0.51	0.71	0.3	A7-D2
28	ML4631 - 34	2(d)	0.60	0.80	0.3	A7-D2
29	ML4631 - 36	2(e)	0.40	0.60	0.3	A7-D2
30	ML4631 - 43	2(f)	1.00	1.20	0.3	A7-D2
31	ML4631 - 56	2(g)	0.73	0.93	0.3	A7-D2
32	ML4631 - 91	2(h)	0.51	0.71	0.3	A7-D2
33	ML4631 - 92	2(i)	0.51	0.71	0.3	A7-D2
34	ML4631 - 94	2(j)	0.38	0.58	0.3	A7-D2
35	ML4631 - 95	2(k)	0.38	0.58	0.3	A7-D2
36	ML4631 - 96	2(l)	0.38	0.58	0.3	A7-D2



PAGE 7

ISSUE 1

#### **TABLE 1(a) - TYPE VARIANTS**

(1) VARIANT	(2) BASED ON TYPE	(3) FIGURE	(4) TOTAL CAPACITANCE C <sub>T</sub> (pF)		(5) JUNCTION CAPACITANCE C <sub>J</sub> (pF)	(6) BODY-LID AND LEAD MATERIAL
			MIN	MAX	(Typical)	AND FINISH
37	ML4631 - 97	2(m)	0.38	0.58	0.3	A7-D2
38	ML4631 - 101	2(n)	0.70	0.90	0.3	A7-D2
39	ML4631 - 103	2(0)	0.51	0.71	0.3	A7-D2
40	ML4631 - 118	2(p)	0.45	0.65	0.3	A7
41	ML4631 - 120	2(q)	0.36	0.56	0.3	D2
42	ML4631 - 128	2(r)	0.46	0.66	0.3	A7-D2
43	ML4631 - 138	2(s)	0.41	0.61	0.3	A7
44	ML4631 - 148	2(t)	0.49	0.69	0.3	A7
45	ML4631 - 255	2(u)	0.50	0.70	0.3	<b>A</b> 7
46	ML4631 - 275	2(v)	0.58	0.78	0.3	A7
47	ML4631 - 276	2(w)	0.36	0.56	0.3	D2
48	ML4631 - 186	2(x)	0.35	0.55	0.3	D2

#### **TABLE 1(b) - MAXIMUM RATINGS**

No.	CHARACTERISTIC	SYMBOL	MAXIMUM RATINGS	UNIT	REMARKS
1	D.C. Reverse Voltage	V <sub>R</sub>	- 200	V	Note 1
2	D.C. Forward Current (Continuous)	l <sub>F</sub>	200	mA	Note 1
3	R.F. Power Dissipation Variants 01 to 23 Variant 24 Variants 25 to 47 Variant 48	P <sub>tot</sub>	5.0 0.6 5.0 0.6	W	Note 1
4	Operating Temperature Range	T <sub>op</sub>	-65 to +150	°C	T <sub>case</sub>
5	Storage Temperature Range	T <sub>stg</sub>	-65 to +150	°C	
6	Soldering Temperature	T <sub>sol</sub>	+ 230	°C	Note 2

#### NOTES


- 1. At  $T_{case} = +25$ °C. For derating at  $T_{case} > +25$ °C, see Figure 1.
- 2. Duration 5 seconds maximum (at a distance of not less than 1.5mm from the body for Variants 23, 24, 47, 48, 71 and 72) and the same termination shall not be resoldered until 3 minutes have elapsed.





PAGE 8

ISSUE -

# FIGURE 1 - PARAMETER DERATING INFORMATION

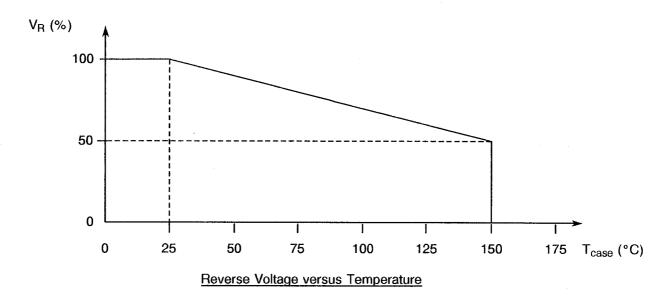

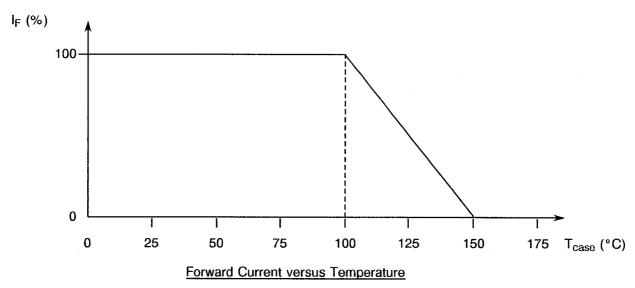

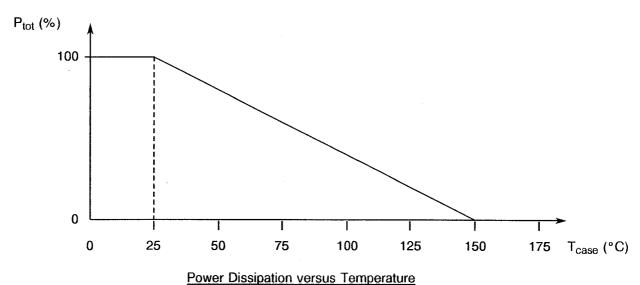




PAGE 9

ISSUE 1

# FIGURE 2 - PHYSICAL DIMENSIONS

# FIGURE 2(a) - VARIANTS 01, 25



MILLIMETRES			
SYMBOL	MIN	MAX	
Α	5.20	5.72	
В	2.16	2.46	
B1	0.41	0.61	
B2	0.15	0.25	
Ød	1.52	1.63	
ØD	3.00	3.23	


1.95


1.52

2.11


1.63

ØD1

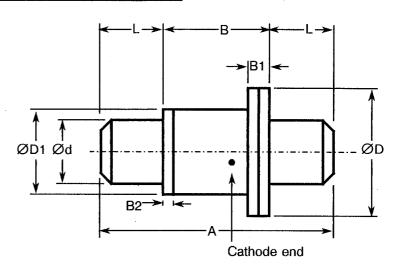





# FIGURE 2(b) - VARIANTS 02, 26



SYMBOL	MILLIMETRES		
STINDOL	MIN	MAX	
Α	2.16	2.46	
B1	0.41	0.61	
B2	0.15	0.25	
ØD	3.00	3.23	
ØD1	1.95	2.11	

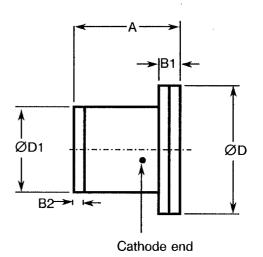






PAGE 10


ISSUE 1

# FIGURE 2 - PHYSICAL DIMENSIONS (CONTINUED)

# FIGURE 2(c) - VARIANTS 03, 27

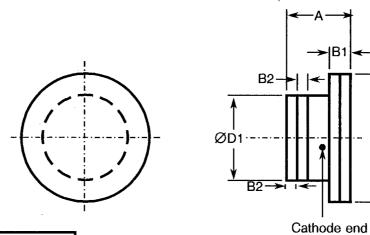


SYMBOL	MILLIMETRES		
STIVIDOL	MIN	MAX	
Α	1.37	1.68	
B1	0.41	0.61	
B2	0.15	0.20	
ØD	3.00	3.23	
ØD1	1.95	2.11	




ØD

# FIGURE 2(d) - VARIANTS 04, 28

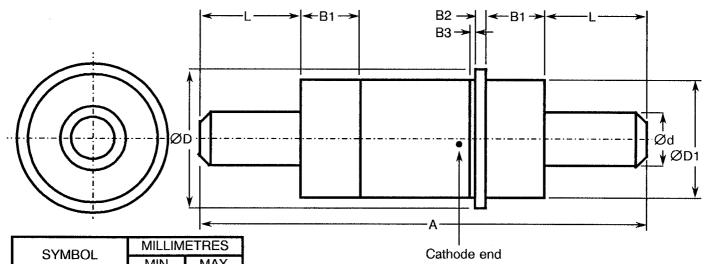

SYMBOL	MILLIMETRES		
O TIVIDOL	MIN	MAX	
Α	19.45	20.12	
B1	2.54	-	
B2	0.53	0.83	
B3	0.19	0.41	
Ød	2.33	2.44	
ØD	-	6.10	
ØD1	5.20	5.46	
L	4.57	4.83	






PAGE 11


ISSUE 1


# FIGURE 2 - PHYSICAL DIMENSIONS (CONTINUED)

# FIGURE 2(e) - VARIANTS 05, 29



SYMBOL	MILLIMETRES		
STIVIDUL	MIN	MAX	
Α	3.60	4.18	
В	2.16	2.46	
B1	0.41	0.61	
B2	0.15	0.25	
Ød	1.52	1.63	
ØD	3.00	3.23	
ØD1	1.95	2.11	
L	1.52	1.63	

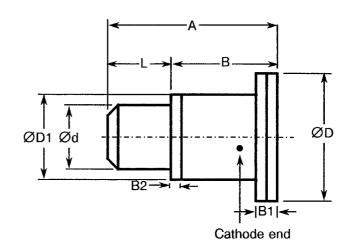






PAGE 12


ISSUE 1

# FIGURE 2 - PHYSICAL DIMENSIONS (CONTINUED)

#### FIGURE 2(f) - VARIANTS 06, 30

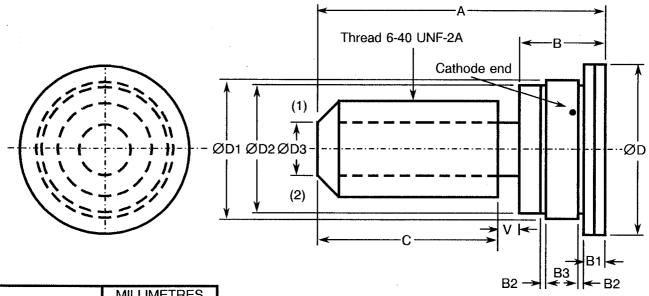

SYMBOL	MILLIMETRES		
OTWIDOL	MIN	MAX	
Α	11.18	11.68	
В	3.02	3.66	
B1	0.64	0.89	
B2	0.18	0.23	
B3	1.17	1.27	
C	6.50	7.90	
ØD	6.48	6.73	
ØD1	5.20	5.50	
ØD2	4.80	5.20	
ØD3	2.00	2.70	
V	0.76	1.02	



#### **NOTES**

- 1. Spline socket to fit S-072 Bristol spline key 1.78mm deep.
- 2. 0.51mm x 45°.




PAGE 13


ISSUE 1

# FIGURE 2 - PHYSICAL DIMENSIONS (CONTINUED)


# FIGURE 2(g) - VARIANTS 07, 31

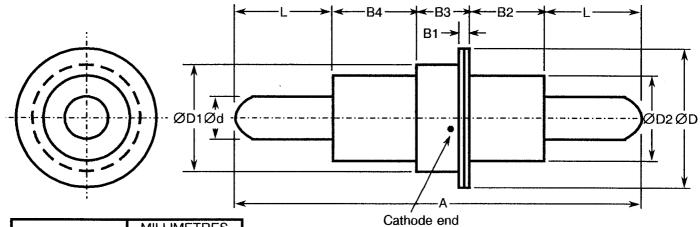


SYMBOL	MILLIMETRES	
STWIDGE	MIN	MAX
Α	19.46	20.12
B1	-	0.76
B2	3.00	3.60
B3	2.41	2.67
B4	3.68	3.94
Ød	2.33	2.39
ØĐ	-	6.10
ØD1	4.72	4.83
ØD2	3.81	4.19
L	4.57	4.83




# FIGURE 2(h) - VARIANTS 08, 32



SYMBOL	MILLIMETRES		
STWIBOL	MIN	MAX	
Α	2.92	3.28	
В	1.40	1.65	
B1	0.41	0.61	
B2	0.15	0.20	
Ød	1.52	1.63	
ØD	3.00	3.23	
ØD1	1.95	2.11	
ØD2	1.85	2.03	
L	1.52	1.63	

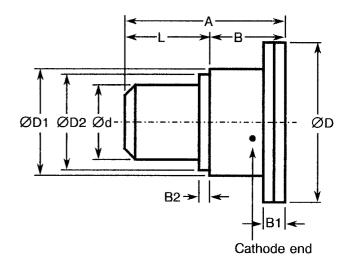






PAGE 14


ISSUE 1

# FIGURE 2 - PHYSICAL DIMENSIONS (CONTINUED)

# FIGURE 2(i) - VARIANTS 09, 33



SYMBOL	MILLIMETRES		
STIVIBOL	MIN	MAX	
Α	4.42	4.93	
В	1.40	1.65	
B1	0.41	0.61	
B2	0.15	0.20	
Ød	1.52	1.63	
ØD	3.00	3.23	
ØD1	1.95	2.11	
L	1.52	1.63	

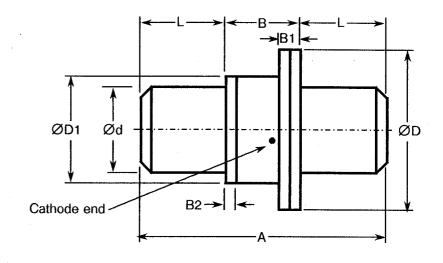







FIGURE 2(i) - VARIANTS 10, 34



SYMBOL	MILLIMETRES		
STIVIBUL	MIN	MAX	
Α	1.02	1.27	
B1	-	0.38	
B2	0.10	0.25	
ØD	1.98	2.18	
ØD1	1.19	1.35	








PAGE 15

ISSUE 1


# FIGURE 2 - PHYSICAL DIMENSIONS (CONTINUED)

# FIGURE 2(k) - VARIANTS 11, 35




<u> </u>	W77.0 10 TO		— <i>/</i>	\   /	Cathode end
ØD	ØD1 -	•			 - Ød
	<u></u> B2→			<b>←</b> B1	<b>A</b>
		<b>←</b> B	· <del></del>		

SYMBOL	MILLIMETRES		
3 TWIDOL.	MIN	MAX	
Α	1.78	2.03	
B.	1.02	1.27	
B1	-	0.38	
B2	0.10	0.25	
Ød	0.61	0.66	
ØD	1.98	2.18	
ØD1	1.19	1.35	




# FIGURE 2(I) - VARIANTS 12, 36



A	Cathode end
$\varnothing D$ $\varnothing D1$ $\varnothing d$ $\bigcirc$	
B	<b>←</b> B1

SYMBOL	MILLIMETRES		
STIVIDOL	MIN	MAX	
Α	1.78	2.03	
В	1.02	1.27	
B1	-	0.38	
B2	0.10	0.25	
Ød	0.61	0.66	
ØD	1.98	2.18	
ØD1	1.19	1.35	







PAGE 16
ISSUE 1

FIGURE 2 - PHYSICAL DIMENSIONS (CONTINUED)

# FIGURE 2(m) - VARIANTS 13, 37



SYMBOL	MILLIMETRES		
STIVIBOL	MIN	MAX	
Α	2.54	2.79	
В	1.02	1.27	
B1	-	0.38	
B2	0.10	0.25	
Ød	0.61	0.66	
ØD	1.98	2.18	
ØD1	1.19	1.35	

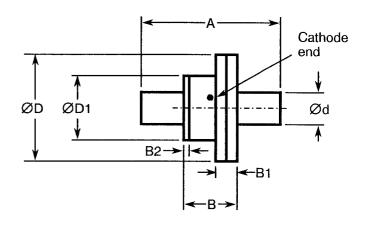






FIGURE 2(n) - VARIANTS 14, 38



SYMBOL	MILLIMETRES		
STIVIBUL	MIN	MAX	
Α	5.34	5.74	
В	2.52	2.72	
B1	0.61	0.81	
B2	0.65	0.85	
С	1.68	2.58	
ØD	4.03	4.09	
ØD1	3.05	3.25	
ØD2	1.60	2.00	
V	0.64	0.94	

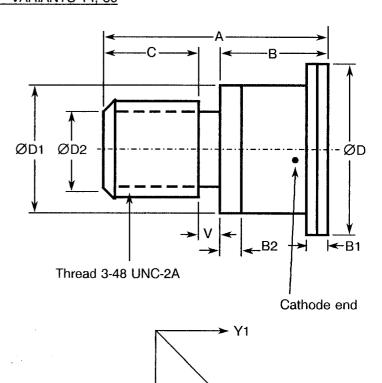

**Z**2


X1




PAGE 17
ISSUE 1


FIGURE 2 - PHYSICAL DIMENSIONS (CONTINUED)

#### FIGURE 2(o) - VARIANTS 15, 39




SYMBOL	MILLIMETRES		
3 TIVIBUL	MIN	MAX	
Α	4.71	5.30	
В	1.47	1.80	
B1	0.41	0.61	
B2	0.20	0.30	
C	1.97	3.19	
ØD	3.00	3.23	
ØD1	2.49	2.59	
ØD2	1.60	2.00	
V	0.64	0.94	

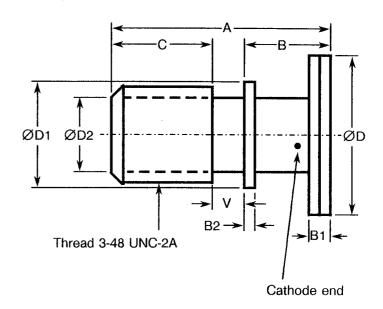





# FIGURE 2(p) - VARIANTS 16, 40



SYMBOL	MILLIMETRES		
STWIBOL	MIN	MAX	
Α	4.19	4.70	
В	0.77	1.04	
B1	0.20	0.30	
B2	0.22	0.28	
С	2.21	3.29	
C1	0.38	0.64	
Ød	1.22	1.32	
ØD	2.49	2.59	
ØD1	1.60	2.00	
Q	0.64	1.14	
V	0.64	0.94	

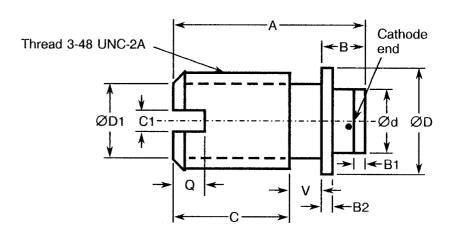






PAGE 18

ISSUE 1


# FIGURE 2 - PHYSICAL DIMENSIONS (CONTINUED)

# FIGURE 2(q) - VARIANTS 17, 41




	<b>-</b>	к——А—		<b>&gt;</b>	
Cathode end		•			- ØD
B2→		→	В	1	<u></u> ✓


SYMBOL	MILLIMETRES		
	MIN	MAX	
Α	1.02	1.27	
B1	0.23	0.33	
B2	0.10	0.15	
ØD	1.29	1.40	




# FIGURE 2(r) - VARIANTS 18, 42

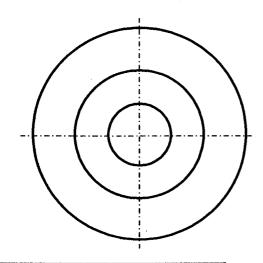

SYMBOL	MILLIMETRES		
STIVIDOL	MiN	MAX	
Α	1.384	1.715	
В	0.749	0.826	
B1	0.025	0.038	
B2	0.05	0.18	
Ød	0.56	0.71	
ØD	1.96	2.11	
ØD1	1.19	1.35	
Q	0.038	0.076	
L	0.558	0.996	

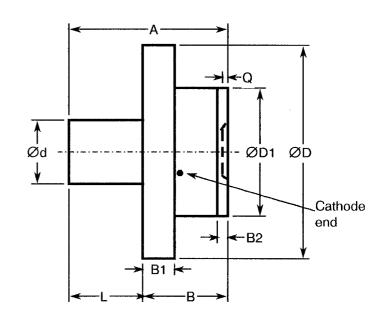






PAGE 19


ISSUE 1

FIGURE 2 - PHYSICAL DIMENSIONS (CONTINUED)

#### FIGURE 2(s) - VARIANTS 19, 43




SYMBOL	MILLIMETRES		
STINEOL	MIN	MAX	
Α	3.56	3.68	
B1	0.20	0.30	
B2	0.46	0.56	
C	2.36	3.02	
C1	0.38	0.64	
Ød	0.69	0.86	
ØD	2.87	3.00	
ØD1	1.60	2.00	
L	0.41	0.48	
Q	0.64	1.14	
V	0.20	0.64	

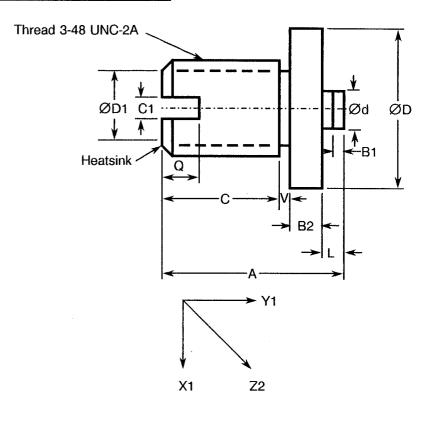


**NOTES** 1. Due to its small size, this package will not be marked.

#### FIGURE 2(t) - VARIANTS 20, 44



SYMBOL	MILLIMETRES		
STWIBOL	MIN	MAX	
Α	4.24	4.75	
В	1.02	1.32	
B1	0.20	0.30	
B2	0.46	0.56	
С	2.74	3.65	
C1	0.38	0.64	
Ød	1.22	1.32	
ØD	2.87	3.00	
ØD1	1.60	2.00	
Q	0.89	1.14	
V	0.64	0.89	

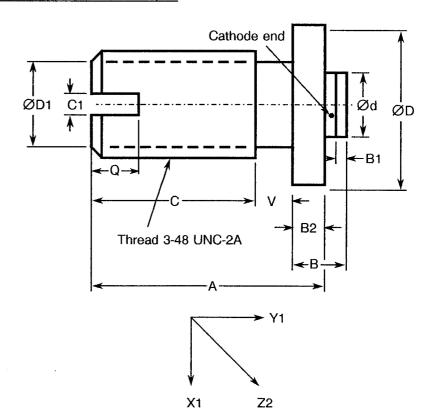




PAGE 20


ISSUE 1

# FIGURE 2 - PHYSICAL DIMENSIONS (CONTINUED)


# FIGURE 2(u) - VARIANTS 21, 45

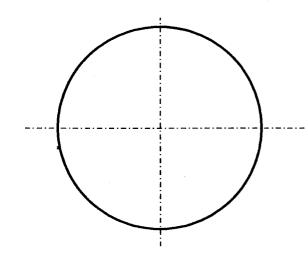


SYMBOL	MILLIMETRES		
	MIN	MAX	
Α	1.14	1.40	
B1	0.23	0.33	
B2	0.15	0.20	
ØD	1.90	2.16	

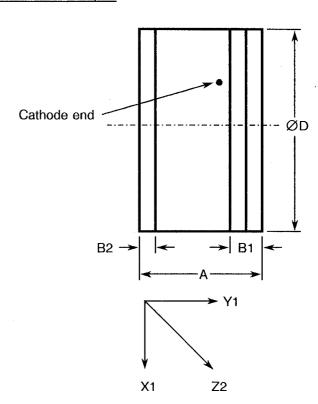


# FIGURE 2(v) - VARIANTS 20, 44



SYMBOL	MILLIMETRES	
STIVIDOL	MIN	MAX
Α	4.04	4.55
В	0.84	1.12
B1	0.20	0.30
B2	0.46	0.56
С	2.54	3.45
C1	0.38	0.64
Ød	1.22	1.32
ØD	2.87	3.00
ØD1	1.60	2.00
Q	0.89	1.14
V	0.64	0.94

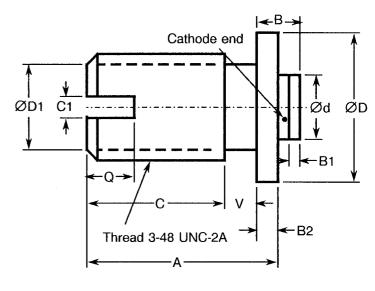







PAGE 21

ISSUE 1


# FIGURE 2 - PHYSICAL DIMENSIONS (CONTINUED)

# FIGURE 2(w) - VARIANTS 23, 47

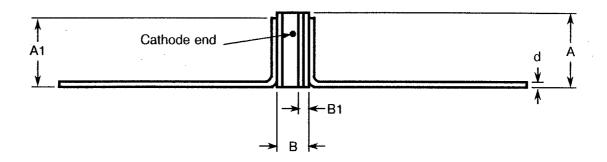

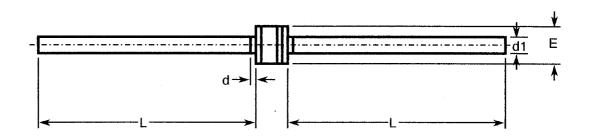

SYMBOL	MILLIMETRES		
STWIBOL	MIN	MAX	
Α	1.35	2.54	
A1	-	2.46	
В	1.02	1.27	
B1	-	0.38	
d	0.07	0.15	
d1	0.38	0.64	
Ε	1.29	1.40	
L	6.10	12.40	






PAGE 22


ISSUE 1

#### FIGURE 2 - PHYSICAL DIMENSIONS (CONTINUED)

#### FIGURE 2(x) - VARIANTS 24, 48

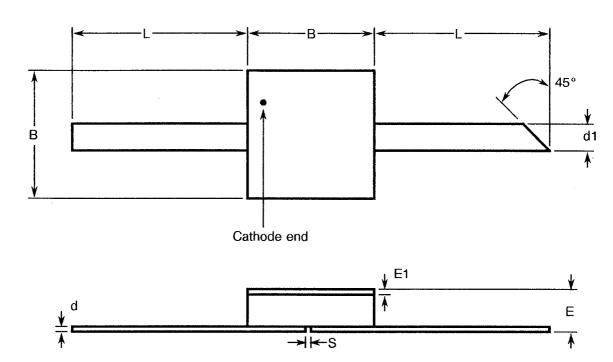

SYMBOL	MILLIMETRES		
	MIN	MAX	
В	2.39	2.62	
d	0.07	0.15	
d1	0.48	0.56	
E	0.79	1.12	
E1 .	0.10	0.18	
L	3.30	5.84	
S	0.10	-	



# **FIGURE 3 - FUNCTIONAL DIAGRAM**



- 1. Anode
- 2. Cathode

#### **NOTES**

- 1. The cathode end shall be marked with a black dot or band. The marking will not be on the cathode connection but adjacent to it.
- 2. The heatsink end shall be the same as the anode end.



Rev. 'B'

PAGE 23

ISSUE 1

#### 4. **REQUIREMENTS**

#### 4.1 GENERAL

The complete requirements for procurement of the diodes specified herein shall be as stated in this specification and ESA/SCC Generic Specification No. 5010 for Discrete Microwave Semiconductor Components. Deviations from the Generic Specification applicable to this specification only, are listed in Para. 4.2.

Deviations from the applicable Generic Specification and this Detail Specification, formally agreed with specific Manufacturers on the basis that the alternative requirements are equivalent to the ESA/SCC requirements and do not affect the components' reliability, are listed in the appendices attached to this specification.

#### 4.2 <u>DEVIATIONS FROM GENERIC SPECIFICATION</u>

#### 4.2.1 Deviations from Special In-process Controls

- (a) Para. 5.2.2, Total Dose Irradiation Testing: Shall be performed during qualification and extension of qualification.
- (b) Para. 5.2.2, Total Dose Irradiation Testing: Shall be performed during procurement on a lot acceptance basis at the total dose irradiation level specified in the purchase order.
- (c) Para. 5.3, Wafer Lot Acceptance: Shall be performed as an S.E.M. Inspection only.

#### 4.2.2 Deviations from Final Production Tests (Chart II)

- (a) Para. 6.2, Pre-burn-in: Shall be performed in accordance with Para. 9.21(a).
- (b) Para. 9.1, Internal Visual Inspection: For Variants 19 and 43, the 3 devices prepared for the Bond Strength Test shall be exempt from the maximum height of bond wire above die requirement.
- (c) Para. 9.2.1, Bond Strength: For Variants 19 and 43, 3 devices shall have bonds which are long enough to permit this test to be performed.
- (d) Para. 9.2.2, Die Shear: Shall not be performed and no additional thermal tests shall be performed to replace this test.
- (e) Para. 9.14, Vibration, Variable Frequency: Shall not be performed.

#### 4.2.3 Deviations from Burn-in and Electrical Measurements (Chart III)

(a) Para. 7.1.1(a), High Temperature Reverse Bias Burn-in: Shall be performed at 50% of rated V<sub>R</sub>.

#### 4.2.4 Deviations from Qualification Tests (Chart IV)

- (a) Para. 9.2.3, Bond Strength: Shall not be performed.
- (b) Para. 9.2.4, Die Shear: Shall not be performed. Thermal resistance measurements shall be performed in accordance with Table 2 of this specification.
- (c) Para. 9.2.3, Special Testing: Shall not be performed.

#### 4.2.5 Deviations from Lot Acceptance Tests (Chart V)

(a) Para. 9.2.3, Special Testing: Shall not be performed.



PAGE 24

ISSUE 1

#### 4.3 MECHANICAL AND ENVIRONMENTAL REQUIREMENTS

#### 4.3.1 <u>Dimension Check</u>

The dimensions of the diodes specified herein shall be checked. They shall conform to those shown in Figure 2.

#### 4.3.2 Weight

The maximum weight of the diodes specified herein shall be:

Variant No.	Weight (g)
01, 25	0.12
02, 26	0.06
03, 27	0.08
04, 28	2.14
05, 29	0.10
06, 30	1.10
07, 31	1.80
08, 32	0.11
09, 33	0.13
10, 34	0.013
11, 35	0.015
12, 36	0.015

Variant No.	Weight (g)
13, 37	0.022
14, 38	0.24
15, 39	0.14
16, 40	0.14
17, 41	0.014
18, 42	0.12
19, 43	0.15
20, 44	0.15
21, 45	0.08
22, 46	0.15
23, 47	0.025
24, 48	0.06

#### 4.3.3 <u>Terminal Strength</u>

The requirements for terminal strength testing are specified in Section 9 of ESA/SCC Generic Specification No. 5010. The test conditions shall be as follows:-

#### (a) Condition: 'A' (Tension)

Variants 23 and 47:

Force: 1.22N.

Duration: 5 seconds.

Variants 24 and 48:

Force: 5.1N.

- Duration: 5 seconds.

#### (b) Condition: 'D2' (Stud Torque)

Variants 06 and 30:

Torque: 70mNm.

Duration: 5 seconds.



PAGE 25

ISSUE

Variants 14, 15, 38 and 39:

- Torque: 56mNm.

Duration: 5 seconds.

Variants 16, 19, 20, 22, 40, 43, 44 and 46:

Torque: 42mNm.

Duration: 5 seconds.

#### (c) Condition: Compression

Variants 01, 02, 03, 04, 05, 06, 07, 08, 09, 14, 15, 18, 21, 25, 26, 27, 28, 29, 30, 31, 32, 33, 38, 39, 42 and 45:

Force: 50N.

- Duration: 5 seconds.

Variants 10, 11, 12, 13, 16, 17, 20, 22, 34, 35, 36, 37, 40, 41, 44 and 46:

Force: 10N.

Duration: 5 seconds.

Variants 19 and 43:

Force: 5N.

Duration: 5 seconds.

The compression test shall be performed by applying the specified force to the end-cap by means of a suitable weight applied for the specified time. On completion of the test, a visual examination shall be performed to check for damage to the end-cap or the ceramic body.

#### 4.4 MATERIALS AND FINISHES

The materials and finishes shall be as specified herein. Where a definite material is not specified, a material which will enable the diodes specified herein to meet the performance requirements of this specification shall be used. Acceptance or approval of any constituent material shall not guarantee acceptance of the finished product.

#### 4.4.1 Case

The case shall be hermetically sealed and have a ceramic body. The lid shall be welded or preform soldered.

#### 4.4.2 Lead Materials and Finish

- (a) For Variants 01, 02, 03, 04, 05, 06, 07, 08, 09, 10, 11, 12, 13, 14, 15, 18, 25, 26, 27, 28, 29, 30, 31, 32, 33, 34, 35, 36, 37, 38, 39 and 42, the body material shall be Type 'A' with Type '7' finish and the lid material shall be Type 'D' with Type '2' finish, in accordance with the requirements of ESA/SCC Basic Specification No. 23500.
- (b) For Variants 16, 19, 20, 21, 22, 40, 43, 44, 45 and 46, the lead material shall be Type 'A' with Type '7' finish in accordance with the requirements of ESA/SCC Basic Specification No. 23500.
- (c) For Variants 17, 23, 24, 41, 47 and 48, the lead material shall be Type 'D' with Type '2' finish in accordance with the requirements of ESA/SCC Basic Specification No. 23500.



PAGE 26

ISSUE 1

#### 4.5 MARKING

#### 4.5.1 General

The marking of components delivered to this specification shall be in accordance with the requirements of ESA/SCC Basic Specification No. 21700 and the following paragraphs. When the component is too small to accommodate all of the marking specified, as much as space permits shall be marked and the marking information, in full, shall accompany the component in its primary package.

The information to be marked and the order of precedence, shall be as follows:-

- (a) Cathode Identification.
- (b) The SCC Component Number.
- (c) Traceability Information.

#### 4.5.2 Cathode Identification

Cathode identification shall be as shown in Figures 2 and 3 of this specification.

#### 4.5.3 The SCC Component Number

Each component shall bear the SCC Component Number which shall be constituted and marked as follows:

	551300301BF
Detail Specification Number	
Type Variant (see Table 1(a))	
Testing Level (B or C, as applicable)	
Total Dose Irradiation Level (if applicable)	

The Total Dose Irradiation Level designation shall be added for those devices for which a sample has been successfully tested to the level in question. For these devices, a code letter shall be added in accordance with the requirements of ESA/SCC Basic Specification No. 22900.

#### 4.5.4 <u>Traceability Information</u>

Each component shall be marked in respect of traceability information as defined in ESA/SCC Basic Specification No. 21700.

#### 4.6 ELECTRICAL MEASUREMENTS

#### 4.6.1 Electrical Measurements at Room Temperature

The parameters to be measured at room temperature are scheduled in Table 2. Unless otherwise specified, the measurements shall be performed at  $T_{amb}$  = +22 ±3 °C.

#### 4.6.2 <u>Electrical Measurements at High and Low Temperatures</u>

The parameters to be measured at high and low temperatures are scheduled in Table 3. Unless otherwise specified, the measurements shall be performed at +150(+0-3) °C.

#### 4.6.3 Circuits for Electrical Measurements

Circuits for use in performing electrical measurements listed in Table 2 of this specification are shown in Figure 4.



PAGE 27

ISSUE

#### 4.7 BURN-IN TESTS

Burn-in shall be Category 3 of Chart III(a).

#### 4.7.1 Parameter Drift Values

The parameter drift values applicable to burn-in are specified in Table 4 of this specification. Unless otherwise stated, the measurements shall be performed at  $T_{amb}$  = +22±3 °C. The parameter drift values ( $\Delta$ ) applicable to the scheduled parameters shall not be exceeded. In addition to these drift value requirements for a given parameter, the appropriate limit value specified in Table 2 shall not be exceeded.

#### 4.7.2 Conditions for High Temperature Reverse Bias Burn-in

The requirements for the high temperature reverse bias burn-in are specified in Section 7 of ESA/SCC Generic Specification No. 5010. The conditions for high temperature reverse bias burn-in shall be as specified in Table 5(a) of this specification.

#### 4.7.3 Conditions for Power Burn-in

The requirements for power burn-in are specified in Section 7 of ESA/SCC Generic Specification No. 5010. The conditions for power burn-in shall be as specified in Table 5(b) of this specification.

#### 4.7.4 Electrical Circuits for High Temperature Reverse Bias and Power Burn-in

Circuits for use in performing the H.T.R.B and power burn-in tests are shown in Figures 5(a) and 5(b) of this specification.



Rev. 'A'

PAGE 28

ISSUE 1

#### TABLE 2 - ELECTRICAL MEASUREMENTS AT ROOM TEMPERATURE - D.C. PARAMETERS

No	CHARACTERIOTICS	OVANDO	MIL-STD-750	TEST	LIMITS		LINUT
No.	CHARACTERISTICS	SYMBOL	TEST METHOD	CONDITIONS	MIN.	MAX.	UNIT
1	Reverse Current 1	l <sub>R1</sub>	4016	V <sub>R</sub> = -200V	-	10	μΑ
2	Reverse Current 2	I <sub>R2</sub>	4016	V <sub>R</sub> = -100V	-	50	nA
3	Forward Voltage	V <sub>F</sub>	4011	I <sub>F</sub> = 100mA	-	1.0	٧
4	Thermal Resistance	R <sub>TH(J-C)</sub>	3101	I <sub>F</sub> = 1.0A Note 1 Variants 01 to 23 Variant 24 Variants 25 to 47 Variant 48	- - -	25 185 25 185	°C/W

#### NOTES

#### TABLE 2 - ELECTRICAL MEASUREMENTS AT ROOM TEMPERATURE - A.C. PARAMETERS

No.	CHARACTERISTICS	SYMBOL	MIL-STD-750 TEST METHOD	TEST FIG.		LIM	UNIT	
INO.		STVIDOL				MIN.	MAX.	ONT
5	Total Capacitance	C <sub>T</sub>	4001	-	V <sub>R</sub> = -10V f = 1.0MHz	Note	e 1	pF
6	Minority Carrier Lifetime	Շլ	-	4(a)	I <sub>F</sub> = 4.5mA	-	800	ns
7	Forward Slope Resistance	R <sub>FS</sub>	-	4(b)	$I_F$ = 100mA $f_0$ = 500MHz Variants 01 to 24 Variants 25 to 48	- -	0.8 0.7	Ω

#### **NOTES**

1. See Column 4 of Table 1(a).

<sup>1.</sup> Pulsed measurement, pulse width = 4.0μs, p.r.f. = 1.0kHz.



Rev. 'A'

PAGE 29

ISSUE 1

# TABLE 3 - ELECTRICAL MEASUREMENTS AT HIGH AND LOW TEMPERATURES

Na	OLIADA OTEDICTIOS	CVMDOL	SPEC.AND/OR	TEST	LIMITS		UNIT
No.   CHARACTERISTICS   S	TEST METH	TEST METHOD	CONDITIONS	MIN.	MAX.	ONIT	
2	Reverse Current 2	I <sub>R2</sub>	4016	As per Table 2	-	10	μΑ

#### **TABLE 4 - PARAMETER DRIFT VALUES**

No.	CHARACTERISTICS	SYMBOL	SPEC.AND/OR TEST METHOD	TEST CONDITIONS	CHANGE LIMITS (Δ)	UNIT
2	Reverse Current 2	I <sub>R2</sub>	As per Table 2	As per Table 2	± 10 (1) or (2) ± 100 (1)	nA %
3	Forward Voltage	V <sub>F</sub>	As per Table 2	As per Table 2	± 100 (1)	mV

# **NOTES**

- 1.  $\Delta 1 = \Delta 2 = \Delta 3$
- 2. Whichever is the greater, referred to the initial measurement.




PAGE 30


ISSUE

# FIGURE 4 - CIRCUITS FOR ELECTRICAL MEASUREMENTS

#### FIGURE 4(a) - MINORITY CARRIER LIFETIME

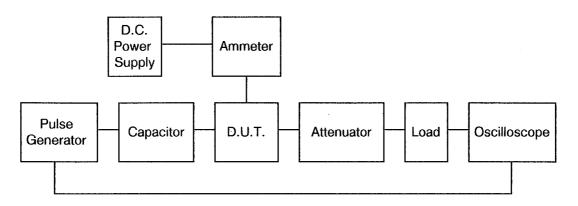

#### FIGURE 4(b) - FORWARD SLOPE RESISTANCE

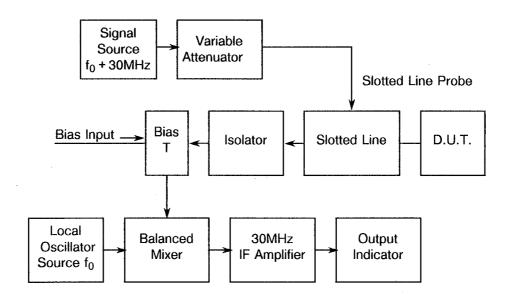



PAGE 31

ISSUE 1

#### TABLE 5(a) - CONDITIONS FOR HIGH TEMPERATURE REVERSE BIAS BURN-IN

No.	CHARACTERISTICS	SYMBOL	CONDITIONS	UNIT
1	Ambient Temperature	T <sub>amb</sub> + 150( + 0 - 3)		°C
2	Reverse Voltage	V <sub>R</sub>	- 100	V


#### TABLE 5(b) - CONDITIONS FOR POWER BURN-IN

No.	CHARACTERISTICS	SYMBOL	CONDITIONS	UNIT
1	Ambient Temperature	T <sub>amb</sub>	+ 125( + 0 - 3)	°C
2	Forward Current	lF	100	mA


#### TABLE 5(c) - CONDITIONS FOR OPERATING LIFE TESTS

No.	CHARACTERISTICS	SYMBOL	CONDITIONS	UNIT
1	Ambient Temperature 1	T <sub>amb1</sub>	+115(+0-3)	°C
2	Forward Current 1	l <sub>F1</sub>	100	mA
3	Ambient Temperature 2	T <sub>amb2</sub>	+ 125( + 0 - 3)	°C
4	Forward Current 2	I <sub>F2</sub>	100	mA

#### FIGURE 5(a) - ELECTRICAL CIRCUIT FOR HIGH TEMPERATURE REVERSE BIAS BURN-IN

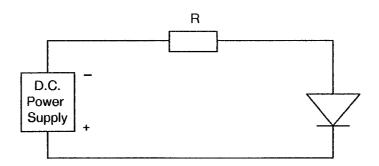

#### FIGURE 5(b) - ELECTRICAL CIRCUIT FOR POWER BURN-IN AND OPERATING LIFE TESTS

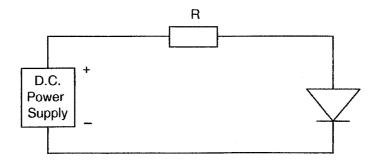



PAGE 32

ISSUE 1

# 4.8 <u>ENVIRONMENTAL AND ENDURANCE TESTS (CHARTS IV AND V OF ESA/SCC GENERIC SPECIFICATION NO. 5010)</u>

#### 4.8.1 Electrical Measurements on Completion of Environmental Tests

The parameters to be measured on completion of environmental tests are scheduled in Table 2. Unless otherwise stated, the measurements shall be performed at  $T_{amb}$  = +22 ±3 °C.

#### 4.8.2 Electrical Measurements at Intermediate Points and on Completion of Endurance Tests

The parameters to be measured at intermediate points and on completion of endurance tests are scheduled in Table 6. Unless otherwise stated, the measurements shall be performed at  $T_{amb} = +22 \pm 3$  °C.

#### 4.8.3 Conditions for Operating Life Tests (Part of Endurance Testing)

The requirements for operating life testing are specified in Section 9 of ESA/SCC Generic Specification No. 5010. The conditions for operating life testing are specified in Table 5(c) of this specification.

#### 4.8.4 Electrical Circuits for Operating Life Tests

The circuit to be used for performance of the operating life test shall be the same as shown in Figure 5(b) for Power Burn-in.

#### 4.9 TOTAL DOSE IRRADIATION TESTING

#### 4.9.1 Application

If specified in Para. 4.2.1 of this specification, total dose irradiation testing shall be performed in accordance with the requirements of ESA/SCC Basic Specification No. 22900.

#### 4.9.2 Bias Conditions

Continuous bias shall be applied during irradiation testing as shown in Figure 6 of this specification.

#### 4.9.3 Electrical Measurements

The parameters to be measured prior to irradiation exposure are scheduled in Table 2 of this specification. Only devices which meet the requirements of Table 2 shall be included in the test sample.

The parameters to be measured during and on completion of irradiation testing are scheduled in Table 7 of this specification.

#### 4.10 SPECIAL TESTING

Not applicable.



Rev. 'A'


PAGE 33

ISSUE 1

# TABLE 6 - ELECTRICAL MEASUREMENTS AT INTERMEDIATE POINTS AND ON COMPLETION OF ENDURANCE TESTING

No.	CHARACTERISTICS	SYMBOL	SPEC. AND/OR TEST METHOD	TEST CONDITIONS	LIMITS MIN. MAX.	UNIT
1	Reverse Current 1	I <sub>R1</sub>	As per Table 2	As per Table 2	As per Table 2	μА
2	Reverse Current 2	I <sub>R2</sub>	As per Table 2	As per Table 2	As per Table 2	nA
3	Forward Voltage	V <sub>F</sub>	As per Table 2	As per Table 2	As per Table 2	٧
5	Total Capacitance	C <sub>T</sub>	As per Table 2	As per Table 2	As per Table 2	pF
7	Forward Slope Resistance	R <sub>FS</sub>	As per Table 2	As per Table 2	As per Table 2	Ω

# FIGURE 6 - BIAS CONDITIONS FOR IRRADIATION TESTING

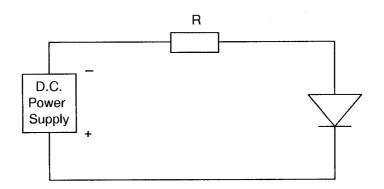

#### NOTES

1. A reverse bias of  $V_R = -100V$  shall be applied.



PAGE 34

ISSUE 1

# TABLE 7 - ELECTRICAL MEASUREMENTS DURING AND ON COMPLETION OF IRRADIATION TESTING

No.	CHARACTERISTICS	SYMBOL	SPEC. AND/OR TEST METHOD	TEST CONDITIONS	CHANGE LIMITS (Δ)	UNIT
6	Minority Carrier Lifetime	Շլ	As per Table 2	As per Table 2	Note 1	%

#### **NOTES**

1. The graph given below shall be used to determine the maximum permitted change.

