



**european space agency
agence spatiale européenne**

Pages 1 to 20

POLYIMIDE INSULATED SHIELDED CABLES

WITH DRAIN WIRE, LOW FREQUENCY,



600V, - 200 TO + 200 °C

BASED ON TYPE SPLD

ESA/SCC Detail Specification No. 3901/021



**space components
coordination group**

Issue/Rev.	Date	Approved by	
		SCCG Chairman	ESA Director General or his Deputy
Issue 1	June 1995		

		ESA/SCC Detail Specification No. 3901/021	PAGE 2 ISSUE 1
--	--	--	---------------------------

DOCUMENTATION CHANGE NOTICE

Rev. Letter	Rev. Date	Reference	CHANGE Item	Approved DCR No.

 SCC	ESA/SCC Detail Specification No. 3901/021	PAGE 3 ISSUE 1
--	--	-------------------

TABLE OF CONTENTS

	<u>Page</u>
1. <u>GENERAL</u>	5
1.1 Scope	5
1.2 Type Variants	5
1.3 Maximum Ratings	5
1.4 Parameter Derating Information	5
1.5 Physical Characteristics	5
1.6 Functional Diagram	5
2. <u>APPLICABLE DOCUMENTS</u>	10
3. <u>TERMS, DEFINITIONS, ABBREVIATIONS, SYMBOLS AND UNITS</u>	10
4. <u>REQUIREMENTS</u>	10
4.1 General	10
4.2 Deviations from Generic Specification	10
4.2.1 Deviations from Special In-process Controls	10
4.2.2 Deviations from Final Production Tests	10
4.2.3 Deviations from Burn-in and Electrical Measurements	10
4.2.4 Deviations from Qualification, Environmental and Endurance Tests	10
4.2.5 Deviations from Lot Acceptance Tests	10
4.3 Mechanical Requirements	11
4.3.1 Dimension Check	11
4.3.2 Weight	12
4.4 Materials and Finishes	12
4.4.1 Conductor	12
4.4.2 Insulation	12
4.4.3 Shield	13
4.4.4 Drain Wire	13
4.4.5 Jacket	13
4.4.6 Construction of Multicore Cables	13
4.4.7 Colour Coding	13
4.5 Marking	14
4.5.1 General	14
4.5.2 The SCC Component Number	14
4.5.3 Characteristics	15
4.5.4 Traceability Information	15
4.5.5 Additional Marking	15
4.6 Electrical Measurements	15
4.6.1 Electrical Measurements at Room Temperature	15
4.6.2 Electrical Measurements at High and Low Temperatures	15
4.6.3 Circuits for Electrical Measurements	15
4.7 Burn-in Tests	15
4.8 Environmental and Endurance Tests	15
4.8.1 Mechanical Properties of Conductor	15
4.8.2 Accelerated Ageing	16
4.8.3 Wrap Test at Ambient Temperature	16
4.8.4 Voltage Test	16
4.8.5 Shrinkage	16
4.8.6 Blocking	16
4.8.7 Cold Bend Test	16

		ESA/SCC Detail Specification No. 3901/021	PAGE 4 ISSUE 1
---	---	--	-------------------

	<u>Page</u>
4.8.8 Cut-through Resistance	18
4.8.9 Notch Resistance	18
4.8.10 Flammability	18
4.8.11 Resistance to Fluids	18
4.8.12 Surface Resistance	18
4.8.13 Abrasion Resistance	18
4.8.14 Soldering	19
4.8.15 Solderability	19
4.8.16 Radiation Resistance	19
4.8.17 Overload Resistance	19
4.8.18 Long-term Ageing Test	19
4.8.19 Anthony and Brown Test	19

TABLES

1(a) Type Variants	6
1(b) Maximum Ratings	8
A Mandrel Diameters and Loads for Finished Wires	16
B Mandrel Diameters and Loads for Shielded and Jacketed Cables	17
C Mandrel Diameters and Loads for Finished Wires or Cores	18
2 Electrical Measurements at Room Temperature	19

FIGURES

1 Parameter Derating Information	8
2 Physical Characteristics	9

APPENDICES (Applicable to specific Manufacturers only)

'A' Agreed Deviations for W.L. GORE & Associates (GmbH)	20
---	----

 SCC	ESA/SCC Detail Specification No. 3901/021	PAGE 5 ISSUE 1
--	--	---------------------------

1. GENERAL

1.1 SCOPE

This specification details the ratings, physical and electrical characteristics, test and inspection data for Polyimide Insulated Cables with Drain Wire, Low Frequency, 600V, -200 to +200 °C, based on Type SPLD. It shall be read in conjunction with ESA/SCC Generic Specification No. 3901, the requirements of which are supplemented herein.

NOTES

1. These cables shall not be used in the presence of hydrazine or nitrogen tetroxide.

1.2 TYPE VARIANTS

Variants of the basic types of cables specified herein which are also covered by this specification, are listed in Table 1(a).

1.3 MAXIMUM RATINGS

The maximum ratings, applicable to the finished cables specified herein, which shall not be exceeded at any time during use or storage in controlled space environment, are scheduled in Table 1(b).

1.4 PARAMETER DERATING INFORMATION

The derating information applicable to the finished wires and cables specified herein is as follows:

- The maximum current for each wire used in a bundle shall be:-

$$I_{Bmax} = I_{max} \times \frac{29 - n}{28} \quad (\text{for } 1 < n < 15)$$

$$I_{Bmax} = \frac{I_{max}}{2} \quad (\text{for } n > 15)$$

where n = number of wires in the bundle;

- The temperature derating information is shown in Figure 1 with maximum current I_{max} for a single wire.
- The derating factors contained herein indicate maximum stress values and do not preclude further derating.

1.5 PHYSICAL CHARACTERISTICS

The physical characteristics of the finished cables specified herein are shown in Figure 2.

1.6 FUNCTIONAL DIAGRAM

Not applicable.



ESA/SCC Detail Specification

No. 3901/021

PAGE 6

ISSUE 1

TABLE 1(a) - TYPE VARIANTS

VARIANT No.	DRAIN WIRE SIZE ISO/(AWG)	DRAIN WIRE No. OF STRANDS x DIAMETER (mm)	No. OF CORES	WIRE SIZE ISO/(AWG)	STRANDING No. OF STRANDS x DIAMETER (mm)	CONDUCTOR CHARACTERISTICS			SHIELD STRAND Ø (mm)	CORE MAX Ø (mm)	FINISHED WIRE OR CABLE CHARACTERISTICS	
						MAX Ø (mm)	NOM SECT. (mm ²)	MAX OHMIC RESISTANCE (Ω/km)			MAX Ø (mm)	MAX WEIGHT (kg/km)
01	- / (30)	07 x 0.102	1	- / (30)	07 x 0.102	0.32	0.057	375	0.063	0.78	1.4	3.4
02	- / (28)	07 x 0.127	1	- / (28)	07 x 0.127	0.39	0.09	253	0.079	0.87	1.6	4.4
03	001/(26)	19 x 0.10 (1)	1	001/(26)	19 x 0.10 (1)	0.47	0.15	157	0.079	0.99	1.8	5.8
04	002/(24)	19 x 0.12 (1)	1	002/(24)	19 x 0.12 (1)	0.58	0.25	111	0.079	1.13	2.1	7.4
05	004/(22)	19 x 0.15 (1)	1	004/(22)	19 x 0.15 (1)	0.76	0.40	58	0.079	1.26	2.4	11
06	006/(20)	19 x 0.20 (1)	1	006/(20)	19 x 0.20 (1)	0.99	0.60	32	0.079	1.48	2.9	17
07	- / (18)	19 x 0.25	1	- / (18)	19 x 0.25	1.29	0.96	21	0.079	1.70	3.9	30
08	012/(16)	19 x 0.30 (1)	1	012/(16)	19 x 0.30 (1)	1.49	1.20	14	0.079	1.98	4.0	34
09	030/(12)	37 x 0.32 (1)	1	030/(12)	37 x 0.32 (1)	2.18	3.00	7.0	0.079	2.70	5.3	66
10	- / (30)	07 x 0.102	2	- / (30)	07 x 0.102	0.32	0.057	383	0.063	0.78	2.2	5.7
11	- / (28)	07 x 0.127	2	- / (28)	07 x 0.127	0.39	0.09	258	0.079	0.87	2.5	7.0
12	001/(26)	19 x 0.10 (1)	2	001/(26)	19 x 0.10 (1)	0.47	0.15	170	0.079	0.99	2.8	9.1
13	002/(24)	19 x 0.12 (1)	2	002/(24)	19 x 0.12 (1)	0.58	0.25	120	0.079	1.13	3.3	11.4
14	004/(22)	19 x 0.15 (1)	2	004/(22)	19 x 0.15 (1)	0.76	0.40	63	0.079	1.26	3.7	17
15	006/(20)	19 x 0.20 (1)	2	006/(20)	19 x 0.20 (1)	0.99	0.60	35	0.079	1.48	4.3	25
16	012/(16)	19 x 0.30 (1)	2	012/(16)	19 x 0.30 (1)	1.49	1.20	15	0.079	1.98	5.9	48
17	030/(12)	37 x 0.32 (1)	2	030/(12)	37 x 0.32 (1)	2.18	3.00	7.5	0.079	2.73	8.0	95
18	- / (30)	07 x 0.102	3	- / (30)	07 x 0.102	0.32	0.057	385	0.063	0.78	2.3	6.7
19	- / (28)	07 x 0.127	3	- / (28)	07 x 0.127	0.39	0.09	259	0.079	0.87	2.7	9.2
20	001/(26)	19 x 0.10 (1)	3	001/(26)	19 x 0.10 (1)	0.47	0.15	171	0.079	0.99	2.9	12
21	002/(24)	19 x 0.12 (1)	3	002/(24)	19 x 0.12 (1)	0.58	0.25	121	0.079	1.13	3.4	15
22	004/(22)	19 x 0.15 (1)	3	004/(22)	19 x 0.15 (1)	0.76	0.40	64	0.079	1.26	3.9	21
23	006/(20)	19 x 0.20 (1)	3	006/(20)	19 x 0.20 (1)	0.99	0.60	37	0.079	1.48	4.6	33

NOTES 1. In accordance with ISO 2635. AWG sizes are given for reference.



ESA/SCC Detail Specification

No. 3901/021

PAGE 7

ISSUE 1

TABLE 1(a) - TYPE VARIANTS (CONTINUED)

VARIANT No.	DRAIN WIRE SIZE ISO(AWG)	DRAIN WIRE No. OF STRANDS x DIAMETER (mm)	No. OF CORES	WIRE SIZE ISO(AWG)	STRANDING No. OF STRANDS x DIAMETER (mm)	CONDUCTOR CHARACTERISTICS			SHIELD STRAND Ø (mm)	CORE MAX Ø (mm)	FINISHED WIRE OR CABLE CHARACTERISTICS	
						MAX Ø (mm)	NOM SECT. (mm ²)	MAX OHMIC RESISTANCE (Ω/km)			MAX Ø (mm)	MAX WEIGHT (kg/km)
24	- / (30)	07 x 0.102	4	- / (30)	07 x 0.102	0.32	0.057	386	0.063	0.78	2.5	8.2
25	- / (28)	07 x 0.127	4	- / (28)	07 x 0.127	0.39	0.09	260	0.079	0.87	2.9	11
26	001/(26)	19 x 0.10 (1)	4	001/(26)	19 x 0.10 (1)	0.47	0.15	171	0.079	0.99	3.2	14
27	002/(24)	19 x 0.12 (1)	4	002/(24)	19 x 0.12 (1)	0.58	0.25	122	0.079	1.13	3.7	18
28	004/(22)	19 x 0.15 (1)	4	004/(22)	19 x 0.15 (1)	0.76	0.40	64	0.079	1.26	4.2	26
29	006/(20)	19 x 0.20 (1)	4	006/(20)	19 x 0.20 (1)	0.99	0.60	37	0.079	1.48	4.9	40
30	001/(26)	19 x 0.10 (1)	5	001/(26)	19 x 0.10 (1)	0.47	0.15	172	0.079	0.99	3.4	17
31	002/(24)	19 x 0.12 (1)	5	002/(24)	19 x 0.12 (1)	0.58	0.25	123	0.079	1.13	4.0	22
32	004/(22)	19 x 0.15 (1)	5	004/(22)	19 x 0.15 (1)	0.76	0.40	64	0.079	1.26	4.5	32
33	006/(20)	19 x 0.20 (1)	5	006/(20)	19 x 0.20 (1)	0.99	0.60	37	0.079	1.48	5.4	49
34	001/(26)	19 x 0.10 (1)	6	001/(26)	19 x 0.10 (1)	0.47	0.15	172	0.079	0.99	3.7	20
35	002/(24)	19 x 0.12 (1)	6	002/(24)	19 x 0.12 (1)	0.58	0.25	124	0.079	1.13	4.4	26
36	004/(22)	19 x 0.15 (1)	6	004/(22)	19 x 0.15 (1)	0.76	0.40	65	0.079	1.26	4.9	37
37	006/(20)	19 x 0.20 (1)	6	006/(20)	19 x 0.20 (1)	0.99	0.60	38	0.079	1.48	5.8	62
38	001/(26)	19 x 0.10 (1)	7	001/(26)	19 x 0.10 (1)	0.47	0.15	172	0.079	0.99	3.7	22
39	002/(24)	19 x 0.12 (1)	7	002/(24)	19 x 0.12 (1)	0.58	0.25	124	0.079	1.13	4.4	28
40	004/(22)	19 x 0.15 (1)	7	004/(22)	19 x 0.15 (1)	0.76	0.40	65	0.079	1.26	4.9	40
41	006/(20)	19 x 0.20 (1)	7	006/(20)	19 x 0.20 (1)	0.99	0.60	38	0.079	1.48	5.8	65

NOTES 1. In accordance with ISO 2635. AWG sizes are given for reference.


TABLE 1(b) - MAXIMUM RATINGS

No.	CHARACTERISTICS	SYMBOL	MAXIMUM RATINGS	UNIT	REMARKS
1	Voltage	V_P	600	Vrms	
2	Maximum Current (Note 1)	I_{max}	1.3 1.5 2.5 3.5 5.0 7.5 10 13 23	A	For AWG 30 28 26 24 22 20 18 16 12
3	Operating Temperature Range	T_{amb}	- 200 to + 200	°C	
4	Storage Temperature Range	T_{stg}	- 200 to + 200	°C	

NOTES

- The above specified current will generate a temperature rise of approximately 50°C above ambient temperature in a vacuum environment. Precautions shall be taken to prevent the total temperature of the wire (ambient plus rise) exceeding the continuous operating temperature of the wire.

FIGURE 1 - PARAMETER DERATING INFORMATION

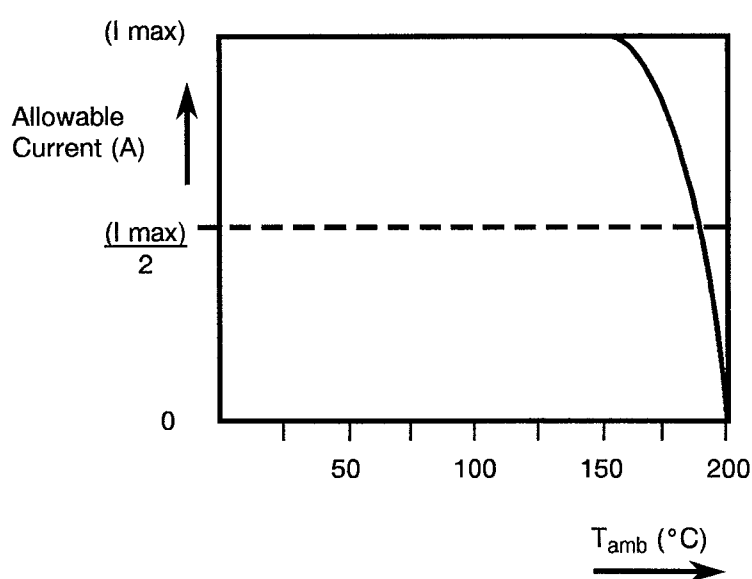

Allowable Current versus Temperature

FIGURE 2 - PHYSICAL CHARACTERISTICS

Dimensions are given in Table 1(a)

FIGURE 2(a) - FINISHED WIRES

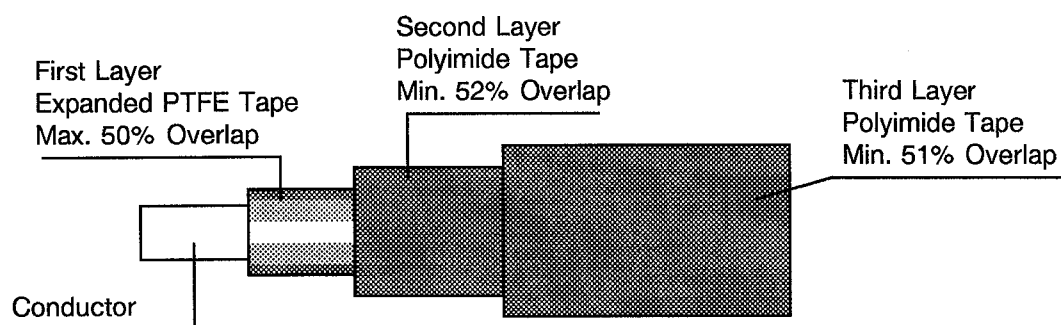


FIGURE 2(b) - SINGLE CABLE WITH SHIELD AND JACKET


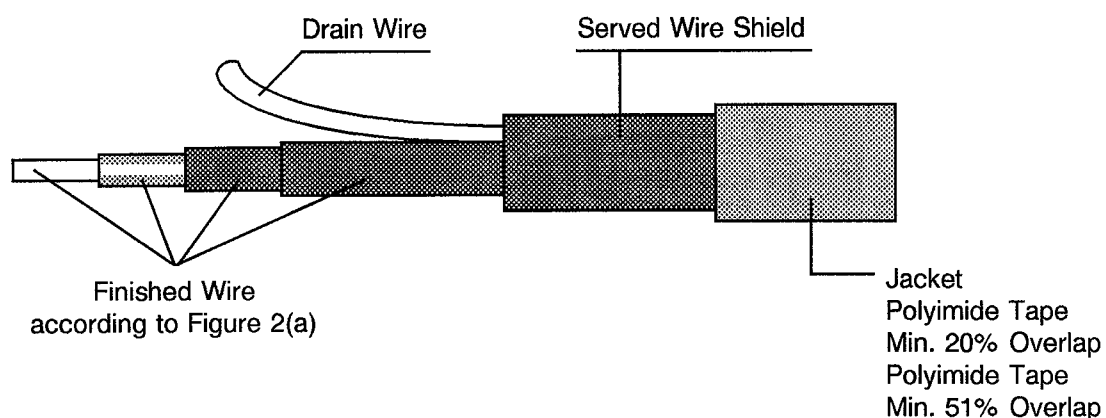


FIGURE 2(c) - MULTICORE CABLE WITH SHIELD AND JACKET

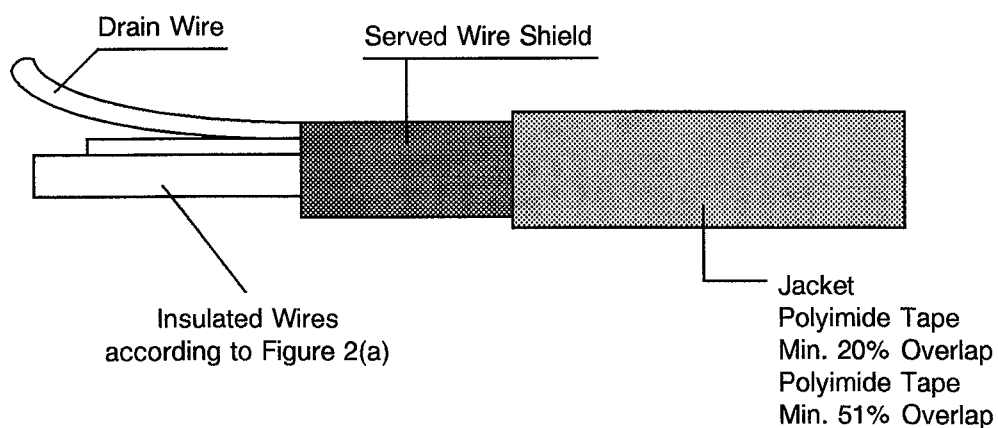

 	ESA/SCC Detail Specification No. 3901/021		PAGE 10 ISSUE 1
---	--	--	----------------------------

2. APPLICABLE DOCUMENTS

The following documents form part of this specification and shall be read in conjunction with it:

- (a) ESA/SCC Generic Specification No. 3901, Wires and Cables, Electrical, 600V, Low Frequency.
- (b) ISO 2635, Conductors for General Purpose Aircraft Electrical Cables and Aerospace Applications - Dimensions and Characteristics.

3. TERMS, DEFINITIONS, ABBREVIATIONS, SYMBOLS AND UNITS

For the purpose of this specification, the terms, definitions, abbreviations, symbols and units specified in ESA/SCC Basic Specification No. 21300 and ESA/SCC Generic Specification No. 3901 shall apply.

4. REQUIREMENTS

4.1 GENERAL

The complete requirements for procurement of the finished cables specified herein are stated in this specification and ESA/SCC Generic Specification No. 3901. Deviations from the Generic Specification, applicable to this specification only, are listed in Para 4.2.

Deviations from the applicable Generic Specification and this Detail Specification, formally agreed with specific Manufacturers on the basis that the alternative requirements are equivalent to the ESA/SCC requirements and do not affect the components' reliability, are listed in the Appendices attached to this specification.

4.2 DEVIATIONS FROM GENERIC SPECIFICATION

4.2.1 Deviations from Special In-process Controls

None.

4.2.2 Deviations from Final Production Tests (Chart II)

None.

4.2.3 Deviations from Burn-in and Electrical Measurements (Chart III)

Not applicable.

4.2.4 Deviations from Qualification, Environmental and Endurance Tests (Chart IV)

- (a) Para. 9.21, Resistance to Fluids: To be modified in accordance with Para. 4.8.11 of this specification.

4.2.5 Deviations from Lot Acceptance Tests (Chart V)

None.

 SCC	ESA/SCC Detail Specification No. 3901/021		PAGE 11 ISSUE 1
--	--	--	--------------------------------------

4.3 MECHANICAL REQUIREMENTS

4.3.1 Dimension Check

The dimensions of the finished wires and cables specified herein shall be checked; they shall conform to those shown in Table 1(a), Figure 2 and Para 4.4 of this specification (see below for the list of parameters to be checked).

LIST OF PARAMETERS TO BE CHECKED

PARAMETER	TABLE 1(a)	FIGURE 2	PARA. 4.4
<u>COMPOSITION</u>			
Number of conductors	X		
Gauge	X		
Shielding	X		
Jacket		X	
<u>CONDUCTOR</u>			
Nature			X
Outer diameter	X		
Number of strands	X		
Strand diameter	X		
Length of lay			X
Silver thickness			X
<u>INSULATION</u>			
Composition		X	X
Thickness			X
Concentricity			X
Outer diameter	X		
Core identification			X
Colour			X
<u>SHIELDING</u>			
Number of strands	X		
Type of shielding			X
Strand diameter	X		
Nature		X	
Shield strand adhesion			X
Shielding lay			X
Shield coverage			X
<u>DRAIN WIRE</u>			
Nature		X	X
Outer diameter	X		
Number of strands	X		
Strand diameter	X		
Length of lay			X
Silver thickness			X
<u>JACKET</u>			
Composition		X	X
Protective Tape Wraps		X	X
Thickness			X
Overlapping		X	
Outer diameter	X		
Colour			X

 	ESA/SCC Detail Specification No. 3901/021		PAGE 12 ISSUE 1
---	--	--	----------------------------

4.3.2 Weight

The maximum weight of the finished cables specified herein shall be as specified in Table 1(a).

4.4 MATERIALS AND FINISHES

The materials and finishes shall be as specified herein. Where a definite material is not specified, a material which will enable the wires and cables specified herein to meet the performance requirements of this specification shall be used. Acceptance or approval of any constituent material does not guarantee acceptance of the finished product.

4.4.1 Conductor

4.4.1.1 Material Characteristics

All strands used in the manufacture of the conductors shall be silver-coated, soft or annealed, high strength copper alloy for ISO 004, 006, 012 and 030, AWG 18 and silver-coated, high strength copper alloy for ISO 001 and 002 and AWG 28 to AWG 30 inclusive. On silver-coated strands, the thickness of silver shall be 2.0µm minimum.

On all copper conductors, any strand shall show a 10% minimum elongation.

For high-strength copper alloy conductors, the tensile characteristics shall be 6% minimum in elongation and 35kg/mm² minimum in tensile strength.

For the determination of the conductor resistance, as mentioned in Para. 9.5 of ESA/SCC Generic Specification No. 3901, the α coefficient for copper alloy is 0.0035.

4.4.1.2 Stranding

The conductors shall be constructed of concentrically laid strands to produce a smooth and uniform conductor of circular cross-section and free from any high strands or other surface irregularities.

The length of lay of the external layer shall not be less than 8, nor more than 16, times the maximum conductor diameter specified in Table 1(a).

4.4.2 Insulation

4.4.2.1 Material

Any insulating material shall be virgin polyimide over expanded PTFE with only those additives that are necessary for processing and pigmentation.

4.4.2.2 Construction

The insulation shall have a uniform cross-section throughout the length of the cables and the conductor shall be evenly centred in the insulation.

The insulation shall consist of 1 wrapped layer of expanded PTFE tape and 2 wrapped layers of polyimide tapes as specified in Figure 2(a).



4.4.3 Shield

4.4.3.1 Material

Shield strands shall meet the requirements for silver-coated, soft or annealed copper outlined in Para. 4.4.1.1 of this specification, but the thickness of silver shall be 2.5µm minimum.

4.4.3.2 Construction

The shield shall be closely and helically wound around the single insulated wire or twisted bundle of insulated wires (core) and provide not less than 92% coverage. The coverage factor K is calculated as follows:-

$$K = \frac{n \times d_w \sqrt{(\pi D)^2 + P^2}}{P \pi D} \times 100(\%)$$

where:-

- K = % coverage
- n = number of serving wires
- d_w = shield strand diameter (mm)
- D = diameter of core (mm)
- P = serving pitch (mm)

4.4.4 Drain Wire

Material, construction, stranding as well as size of the drain wire shall be exactly the same as the conductor of the single insulated wire. It shall be placed underneath the served wire shield.

4.4.5 Jacket

All shielded cables shall be provided with jackets of wrapped polyimide tapes as specified in Figures 2(b) and 2(c). The wrapped tapes shall be heat-sealed. The side of the tape of the first layer above the shield, which is not coated with FEP resin, shall be facing the shield.

The jacket shall have an even wall thickness of 0.1mm.

4.4.6 Construction of Multicore Cables

Multicore cables shall be constructed by twisting the required number and size of finished wires to form a uniform cable without high strands, bends or other irregularities. Finished wires of only one size shall be used for one cable. The cabling shall be with left-hand lay and the length of lay shall not be less than 12, nor more than 16, times the outside diameter of the unshielded,unjacketed cable. The construction of shielded and jacketed cables is shown in Figures 2(b) and 2(c). Fillers shall not be used in the construction of multicore cables except for the 5- and 6-core cables, where the 5/6 wires shall be twisted around a round, uncoloured filler made of expanded polytetrafluorethylene. The diameter of the filler for the 5/6-core cables shall be 0.7/1.0 times the diameter of the wires used in the cables.

4.4.7 Colour Coding

4.4.7.1 Single and Multicore Cable Colour Coding

The colour coding of all cables shall be according to the following list, if not otherwise specified in the contract.

Number of cores in cable	Colour of respective cores						
2	red	natural					
3	red	natural	yellow				
4	red	natural	yellow	green			
5	red	natural	yellow	green	brown		
6	red	natural	yellow	green	brown	black	
7	red	natural	yellow	green	brown	black	orange

4.4.7.2 Jacket Colour

The colour of jackets shall normally be the natural colour of the polyimide tapes.

4.5 MARKING

4.5.1 General

The marking of all spools of finished cables delivered to this specification shall be in accordance with the requirements of ESA/SCC Basic Specification No. 21700. Each spool shall be marked in respect of:-

- (a) The SCC Component Number.
- (b) Characteristics.
- (c) Traceability Information.
- (d) Additional Marking.

4.5.2 The SCC Component Number

Each spool shall bear the SCC Component Number which shall be constituted and marked as follows:-

390102101B

Detail Specification Number _____

Type Variant (see Table 1(a)) _____

Testing Level _____

 	ESA/SCC Detail Specification No. 3901/021		PAGE 15 ISSUE 1
---	--	--	----------------------------

4.5.3 Characteristics

The characteristics shall show the length(s) of the finished cable wound on each spool and shall be marked as follows:-

Length in metres (see Note) _____ 100m
 Symbol for metres _____

NOTES

1. Whenever the length is less than 100 metres, insert a zero in the first block (example: 075 m).
 If more than one length of finished cable is wound on a spool, the characteristics of each length shall be marked as above.

4.5.4 Traceability Information

Each spool shall be marked in respect of traceability information in accordance with the requirements of ESA/SCC Basic Specification No. 21700.

4.5.5 Additional Marking

Each spool shall bear the Manufacturer's Quality Control Inspector's stamp or initials.

4.6 ELECTRICAL MEASUREMENTS

4.6.1 Electrical Measurements at Room Temperature

The parameters to be measured at room temperature are scheduled in Table 2. The measurements shall be performed at $T_{amb} = +22 \pm 3 \text{ }^{\circ}\text{C}$.

4.6.2 Electrical Measurements at High and Low Temperatures

Not applicable.

4.6.3 Circuits for Electrical Measurements

Not applicable.

4.7 BURN-IN TESTS

Not applicable.

4.8 ENVIRONMENTAL AND ENDURANCE TESTS

4.8.1 Mechanical Properties of Conductor

As detailed in Para's 4.4.1.1 and 4.4.4 of this Specification.

4.8.2 Accelerated Ageing

Ageing Temperature $+230 \pm 5$ °C.

TABLE A - MANDREL DIAMETERS AND LOADS FOR FINISHED WIRES

Wire Size ISO/(AWG)	Mandrel Diameter (mm)	Weight (kg)
- /(30)	5.0	0.15
- /(28)	6.0	0.25
001/(26)	6.0	0.25
002/(24)	6.0	0.25
004/(22)	6.0	0.40
006/(20)	6.0	0.40
- /(18)	10	0.50
012/(16)	10	0.50
030/(12)	20	1.00

4.8.3 Wrap Test at Ambient Temperature

The mandrel diameters and applied loads for wrap testing of finished wires are given in Table A. The mandrel diameters and applied loads for screened and jacketed cables are given in Table B.

4.8.4 Voltage Test

No particular conditions are applicable.

4.8.5 Shrinkage

The shrinkage temperature shall be $+200 \pm 5$ °C

4.8.6 Blocking

The blocking temperature shall be $+230 \pm 5$ °C.

4.8.7 Cold Bend Test

The mandrel diameters and loads shall be as specified in Table C.

**TABLE B - MANDREL DIAMETERS AND LOADS FOR SHIELDED
AND JACKETED CABLES**

Cable Size ISO/(AWG)	Number of Cores	Mandrel Diameter (mm)	Load (kg)
- /(30)	1	10	0.15
- /(28)	1	15	0.25
001/(26)	1	15	0.25
002/(24)	1	15	0.25
004/(22)	1	20	0.50
006/(20)	1	25	0.50
- /(18)	1	30	1.00
012/(16)	1	30	1.00
030/(12)	1	40	1.00
- /(30)	2	20	0.25
- /(28)	2	20	0.50
001/(26)	2	20	0.50
002/(24)	2	25	0.50
004/(22)	2	30	0.80
006/(20)	2	35	0.80
012/(16)	2	50	1.00
030/(12)	2	60	1.00
- /(30)	3	15	0.25
- /(28)	3	20	0.50
001/(26)	3	25	0.75
002/(24)	3	30	0.75
004/(22)	3	30	1.20
006/(20)	3	40	1.20
- /(30)	4	20	0.50
- /(28)	4	25	0.80
001/(26)	4	25	1.00
002/(24)	4	30	1.00
004/(22)	4	35	1.50
006/(20)	4	40	1.50
001/(26)	5	25	1.50
002/(24)	5	30	1.50
004/(22)	5	35	2.00
006/(20)	5	40	2.00
001/(26)	6/7	35	1.50
002/(24)	6/7	30	1.50
004/(22)	6/7	35	2.00
006/(20)	6/7	40	2.00

**TABLE C - MANDREL DIAMETERS AND LOADS FOR
FINISHED WIRES OR CORES**

Wire Size ISO/(AWG)	Mandrel Diameter (mm)	Weight (kg)
- /(30)	5.0	0.15
- /(28)	6.0	0.25
001/(26)	6.0	0.25
002/(24)	6.0	0.25
004/(22)	6.0	0.40
006/(20)	6.0	0.40
- /(18)	10	0.50
012/(16)	10	0.50
030/(12)	20	1.00

4.8.8 Cut-through Resistance

The mean load measured during the required tests shall not be less than the relevant value specified below:-

Wire Size ISO	-	-	001	002	004	006	-	012	030
(AWG)	(30)	(28)	(26)	(24)	(22)	(20)	(18)	(16)	(12)
Cut-through Load (kg)	9.0	11	11	11	25	32	32	35	50

4.8.9 Notch Resistance

The depth of notch shall be 0.04mm.

4.8.10 Flammability

No particular conditions are applicable.

4.8.11 Resistance to Fluids

Tests (h), (i) and (j) shall not be performed.

4.8.12 Surface Resistance

No particular conditions are applicable.

4.8.13 Abrasion Resistance

The weight to be applied to the needle is specified below:-

Wire Size ISO	-	-	001	002	004	006	-	012	030
(AWG)	(30)	(28)	(26)	(24)	(22)	(20)	(18)	(16)	(12)
Scrape Abrasion Load (kg)	350	500	650	750	800	900	900	1050	1200

 SCC	ESA/SCC Detail Specification No. 3901/021		PAGE 19 ISSUE 1
---	--	--	----------------------------

4.8.14 Soldering

No particular conditions are applicable.

4.8.15 Solderability

No particular conditions are applicable.

4.8.16 Radiation Resistance

No particular conditions are applicable.

4.8.17 Overload Resistance

No particular conditions are applicable.

4.8.18 Long-term Ageing Test

The long-term ageing temperature shall be +200°C.

4.8.19 Anthony and Brown Test

No particular conditions are applicable.

TABLE 2 - ELECTRICAL MEASUREMENTS AT ROOM TEMPERATURE

No.	CHARACTERISTICS	SPEC. AND/OR TEST METHOD	TEST CONDITION	LIMITS	UNIT
1	Conductor Resistance	ESA/SCC No. 3901, Section 9	Para 9.5	Table 1(a)	Ω/Km
2	Spark Test	ESA/SCC No. 3901, Section 9	Para 9.6	Insulation : 3.0 Jacket : 1.5	kV
3	Voltage Test	ESA/SCC No. 3901, Section 9	Para 9.7	Para 9.7	kV
4	Insulation Resistance	ESA/SCC No. 3901, Section 9	Para 9.8	Insulation : 750 Jacket : 30	MΩ.km
5	Surface Resistance	ESA/SCC No. 3901, Section 9	Para 9.22	: 125	MΩ.mm

 	ESA/SCC Detail Specification No. 3901/021		PAGE 20 ISSUE 1
---	--	--	----------------------------

APPENDIX 'A'

Page 1 of 1

AGREED DEVIATIONS FOR W.L. GORE & ASSOCIATES (GmbH)

ITEMS AFFECTED	DESCRIPTION OF DEVIATIONS
Figure 2	Expanded PTFE tape shall be GORE-TEX ®
Para. 4.4.2.1	Expanded PTFE tape shall be GORE-TEX ®

NOTES

1. GORE-TEX ® = Registered Trade Mark of W.L. Gore and Associates (GmbH).